



Electrically conductive nanomaterials for cardiac tissue engineering

Khadijeh Ashtari^{a,b,c,1}, Hojjatollah Nazari^{b,d,1}, Hyojin Ko^{e,f,1}, Peyton Tebon^{e,f}, Masoud Akhshik^{g,h,u},
Mohsen Akbari^{i,j,k}, Sanaz Naghavi Alhosseini^{l,d}, Masoud Mozafari^{m,n}, Bitia Mehravi^{a,b,c}, Masoud Soleimani^o,
Reza Ardehali^p, Majid Ebrahimi Warkiani^{q,r}, Samad Ahadian^{e,f}, Ali Khademhosseini^{e,f,s,t,*}

^a Radiation Biology Research Center, Iran University of Medical Sciences, Tehran, Iran

^b Faculty of Advanced Technologies in Medicine, Department of Medical Nanotechnology, Iran University of Medical Sciences, Tehran, Iran

^c Cellular and Molecular Research Center, Iran University of Medical Sciences, Tehran, Iran

^d Stem Cell Technology Research Center, Tehran, Iran

^e Center for Minimally Invasive Therapeutics (C-MIT), University of California – Los Angeles, Los Angeles, USA

^f Department of Bioengineering, University of California – Los Angeles, Los Angeles, USA

^g Faculty of Forestry, University of Toronto, Toronto, Canada

^h Center for Biocomposites and Biomaterials Processing (CBBP), University of Toronto, Toronto, Canada

ⁱ Laboratory for Innovations in MicroEngineering (LiME), Department of Mechanical Engineering, University of Victoria, Victoria, Canada

^j Center for Biomedical Research, University of Victoria, Victoria, Canada

^k Center for Advanced Materials and Related Technologies, University of Victoria, Victoria, Canada

^l Biomaterials Group, Department of Biomaterial Engineering, Amirkabir University of Technology, Tehran, Iran

^m Lunenfeld Tanenbaum Research Institute, Mount Sinai Hospital, Toronto, Canada

ⁿ Institute of Biomaterials and Biomedical Engineering, University of Toronto, Toronto, Canada

^o Faculty of Medical Sciences, Department of Hematology and Cell Therapy, Tarbiat Modares University, Tehran, Iran

^p Division of Cardiology, Department of Internal Medicine, David Geffen School of Medicine, University of California – Los Angeles, USA

^q School of Biomedical Engineering, University of Technology Sydney, Sydney, Australia

^r Institute of Molecular Medicine, Sechenov University, Moscow, Russia

^s Department of Chemical and Biomolecular Engineering, University of California – Los Angeles, Los Angeles, USA

^t Department of Radiology, David Geffen School of Medicine, University of California – Los Angeles, Los Angeles, USA

^u Shahdad Ronak Commercialization Company, Tehran, Iran

ARTICLE INFO

Article history:

Received 23 February 2019

Received in revised form 2 June 2019

Accepted 4 June 2019

Available online 6 June 2019

Keywords:

Electrically conductive scaffolds

Cardiac tissue engineering

Carbon-based nanomaterials

Gold nanoparticles

Electroactive polymers

Conductive nanomaterials

Cardiovascular diseases

ABSTRACT

Patient deaths resulting from cardiovascular diseases are increasing across the globe, posing the greatest risk to patients in developed countries. Myocardial infarction, as a result of inadequate blood flow to the myocardium, results in irreversible loss of cardiomyocytes which can lead to heart failure. A sequela of myocardial infarction is scar formation that can alter the normal myocardial architecture and result in arrhythmias. Over the past decade, a myriad of tissue engineering approaches has been developed to fabricate engineered scaffolds for repairing cardiac tissue. This paper highlights the recent application of electrically conductive nanomaterials (carbon and gold-based nanomaterials, and electroactive polymers) to the development of scaffolds for cardiac tissue engineering. Moreover, this work summarizes the effects of these nanomaterials on cardiac cell behavior such as proliferation and migration, as well as cardiomyogenic differentiation in stem cells.

© 2019 Elsevier B.V. All rights reserved.

Contents

1. Introduction	163
2. Biological response of cardiomyocytes to nanomaterials.	163
3. Carbon-based nanomaterials	164
3.1. Carbon nanotubes	164

* Corresponding author at: Center for Minimally Invasive Therapeutics (C-MIT), University of California – Los Angeles, Los Angeles, USA.

E-mail address: khademh@ucla.edu (A. Khademhosseini).

¹ These authors contributed equally to this work

3.2.	Carbon nanofibers	167
3.3.	Graphene and its derivatives	167
4.	Gold nanomaterials	169
5.	Electroactive polymers	172
5.1.	Polypyrrole	172
5.2.	Polyaniline	172
5.3.	Piezoelectric polymeric materials	175
6.	Biocompatibility of electrically conductive nanomaterials	175
7.	Concluding remarks and future challenges	176
	Acknowledgements	176
	References	176

1. Introduction

In the United States cardiovascular diseases (CVDs) are responsible for one death every 40 s [1]. Loss of blood circulation to regions of the heart muscle due to coronary artery occlusion can damage the myocardium, causing electrophysiological and morphological disorders of the heart [2,3]. Ischemia may result in cardiac cell death through necrosis, apoptosis, or autophagy and the subsequent formation of scar tissue reduces the cardiac contractile capacity [4]. Since adult cardiomyocytes have a limited regenerative capacity, the damage can be permanent and lead to heart failure and death [5]. Complex surgical treatments have been developed over the past two decades for cardiac transplantation; however, donor shortage is a major challenge that limits this approach. In addition, transplant patients must receive immunosuppressive drug therapy after surgery to decrease the risk of transplant rejection [5]. The disadvantages of heart transplantations highlight the need for alternative therapies for the prevention and remediation of cardiac failure. In the past decade, regeneration of the heart, using approaches ranging from cell therapy to tissue engineering, has been extensively investigated as an alternative method of managing CVDs. Cardiac cell-based therapy is a concept in which different cell sources such as mesenchymal stem cells (MSCs), induced pluripotent stem cells (iPSCs), and embryonic stem cells (ESCs) [6–9] or their derivatives are used alone, or in combination, with scaffolds to treat the disease [10,11].

In the extracellular matrix (ECM) of the heart, collagen and elastin form fibers which weave to compose a dense, elastic molecular network. The micro- and nanoscale topography of the matrix causes mechanical coupling of cardiomyocytes, providing the unique electrical and mechanical characteristics of the heart [12]. The biochemical, electrical, and mechanical functions of the myocardial ECM are dependent on its nanofeatures [13]. Cardiac tissue engineering can be defined as the field that aims to generate or repair the myocardium by combining knowledge and techniques from materials science, micro/nano-engineering, cellular biology, and biochemistry [14]. The reconstruction of effective cardiac tissue requires proper selection of cell sources, establishment of the myocardial ECM, electromechanical stimulation of cells, fabrication of robust contractile bundles, and inclusion of vascular channels.

Recently, there has been considerable effort to develop functional scaffolds that are designed for cardiac repair, including cardiac patches, injectables, and nanofibrous or nano-patterned scaffolds [15,16]. To improve scaffold functionality, various nanomaterials in the form of nanofibers [11,17–19], mesoporous and composite materials [20], nanoparticles [21], and modified nano-patterned surfaces have been adopted. These technologies help to recreate biomimetic microenvironments for cells to reach their full biological potential in the engineering of a functional myocardium (Fig. 1).

Fabrication of scaffolds is influenced by the integration of chemical, biological, and physical properties [19,22]. An ideal scaffold for cardiac tissue engineering must be electrically conductive, mechanically stable, biocompatible, topographically suitable, and possess similar elasticity to

the native myocardium [23,24]. The material's ability to propagate electrical impulses and translate them into synchronized contractions is necessary to maintain circulation by pumping blood through the organ [25]. Both the engineered cardiac constructs and injected cells must integrate into the electrical syncytium of the myocardium to maintain spontaneous contractile activity [26]. Electroactive biomaterials can transmit electromechanical, electrochemical, and electrical stimulation to cells [27]. In cardiac tissue engineering, development and utilization of electroactive materials (conductive polymers, piezoelectric materials, carbon nanotubes (CNTs), carbon nanofibers, as well as graphene and gold nanostructures) has been a flourishing area of research in recent years. This review summarizes the advancement of electroactive nanomaterials for cardiac regeneration, and highlights the possibility of using these systems to regenerate cardiac tissue (Fig. 2).

2. Biological response of cardiomyocytes to nanomaterials

It is important to understand the role of key genes and signaling pathways in cardiac tissue development and function. These genes and pathways play an important role in nanomaterial interaction with cardiac cells. Cardiomyocytes are formed as a result of cardiac progenitor cell differentiation in the body in which several cardiac transcription factors, such as Tbx5, Nkx-2.5, and GATA-4 help to activate the transcription of structural genes for cardiomyocytes, such as myosin heavy chain, desmin, cardiac troponins, and myosin light chain [28]. The up-regulation of these genes often occurs after 7 days of differentiation on two-dimensional (2D) culture systems. In particular, Nkx-2.5 is expressed in cardiomyocytes with positive cTnT after 10 days of differentiation [29]. Major signaling pathways involved in cardiac differentiation are BMP, FGF, Wnt, and TGFβ/Activin/Nodal pathways. Other molecular pathways include Notch and p38 MAPK signaling pathways [30]. Commonly used differentiation protocols result in a mixture of atrial, ventricular, and nodal cells [31]. However, it is possible to enrich a specific population of cardiomyocytes compared to others. For example, it was shown that BMP antagonist Grem2 is able to preferentially differentiate cardiomyocytes to atrial cell type [32]. Nanomaterials can affect stem cell differentiation toward cardiomyocytes. Moreover, they have shown great promise to maintain the function of primary cardiomyocytes *in vitro* and enhance their function and survival *in vivo*.

Mechanical and electrical integrity of the heart is crucial for cardiomyocyte function. The connexin (Cx) genes encode Cx proteins to link cardiomyocytes in the heart. In particular, Cx43 is synthesized in the plasma membrane of cardiomyocytes making intercellular channels between the cytoplasmic components of neighboring cardiomyocytes [33]. Cx43 plays an important role in direct transferring signaling molecules and ions from the cell membrane. These signaling molecules and ions regulate cell survival and intracellular calcium transition through releasing glutamate and ATP facilitating electrical pulse propagation [34]. Moreover, Cx43 localization on the cell membrane has cardioprotective characteristic and avoids ischemia [35]. Electrically conductive and mechanically strong nanomaterials have shown great

promise to connect individual cardiomyocytes resembling the role of Cx43 in tissue development and function.

Cardiac tissues have been engineered using different sources of cardiomyocytes [36]. Foetal and neonatal cardiomyocytes from animal models, such as rats and mice have largely been used in cardiac tissue engineering as they are easy to obtain and have high regenerative ability [37]. These early stage cardiomyocytes have higher survival rate and regeneration capability compared to adult cardiomyocytes [38]. However, there are some issues regarding the use of primary cardiomyocytes, such as immunogenicity, malignancy, and ethical concern [39]. Nanomaterials can be helpful to remodel the microenvironment of primary cardiomyocytes *in vitro* and enhance their survival and function *in vivo*. Differentiated cardiomyocytes from stem cells, such as MSCs, iPSCs, and ESCs have also shown great promise in cardiac tissue engineering [40]. In particular, cardiomyocyte-derived iPSCs can be obtained from human fibroblasts to make personalized tissue constructs. However, there is still required to enhance the efficiency of differentiation protocols to make highly pure and functional cardiomyocytes. Here, nanomaterials can be useful in regulating stem cell differentiation to cardiomyocytes. Moreover, they can provide reliable and biomimetic scaffolds for engineered cardiac tissues.

3. Carbon-based nanomaterials

3.1. Carbon nanotubes

CNTs have been utilized extensively in biomedical and biological applications such as imaging, regenerative medicine, and pharmaceutical applications like drug delivery [41–43]. CNTs are interesting candidates as substrates or additives in biomaterials for tissue regeneration due to their mechanical and electrical properties [44,45]. These cylindrical nano-structured carbon molecules have a high aspect ratio. There are three classes of CNTs based on the number of graphite cylinders in the structure: single-walled carbon nanotubes (SWCNTs, 1–2 nm diameter), double-walled carbon nanotubes (DWCNTs), and multi-walled carbon nanotubes (MWCNTs, 10–100 nm diameter). The electrical properties of CNTs are influenced by the orientation and wrapping of the hexagonal bond structure. CNTs are known for their mechanical strength and can be integrated into materials to increase the tensile strength and Young's modulus of composites [46]. There are many methods available to produce CNTs including physical methods, such as electric-arc technique [47] and laser ablation [48], and chemical methods, such as chemical vapor deposition [49].

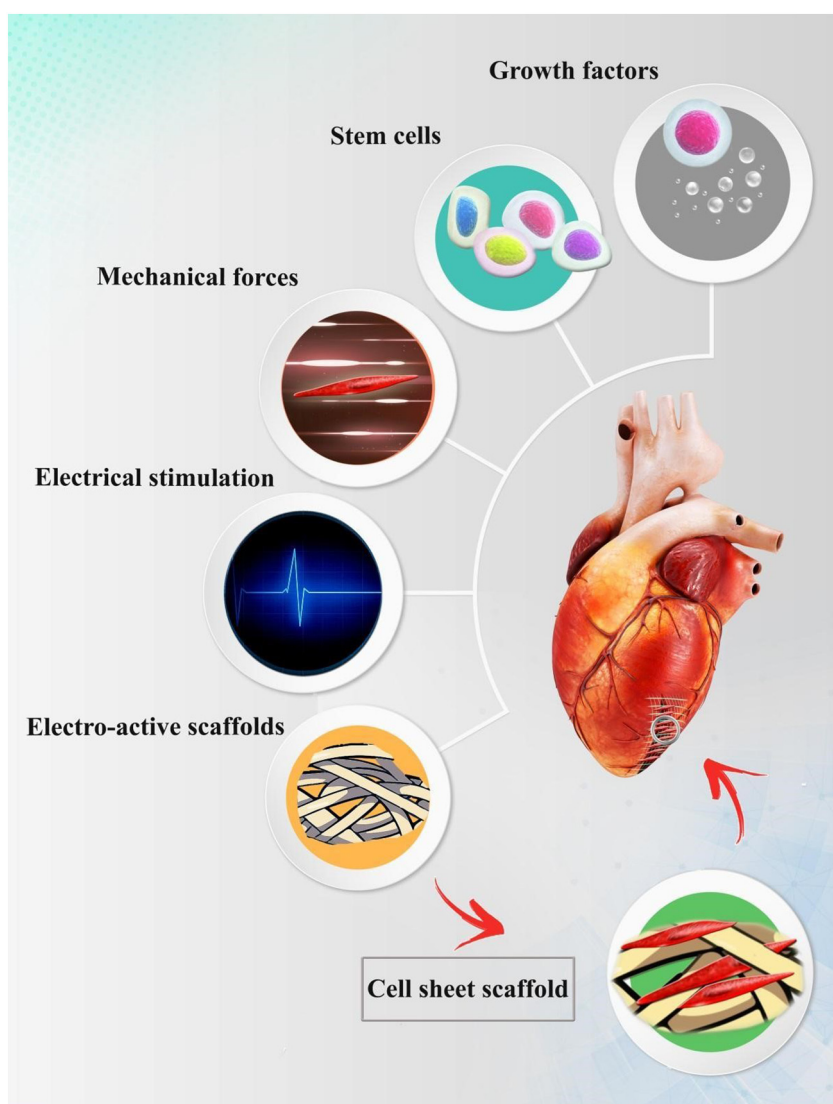


Fig. 1. Representation of key factors for cardiac tissue regeneration. Induced pluripotent, mesenchymal, and embryonic stem cells have been used as cell sources for cardiogenic differentiation using various protocols and growth factors. Mimicking the native cardiomyocyte microenvironment is also crucial for functional tissue regeneration – this can be done by applying relevant mechanical and electrical stimulation through electrically conductive nanoscale scaffolds. Implementing these factors can help to achieve dense populations of beating, functional cardiomyocytes embedded in scaffolds for cardiac regeneration.

CNTs have been used for a wide variety of applications in cellular biology ranging from *in vivo* cell tracking, labeling, and transfection to improving the conductivity of scaffolds [21,50,51]. A major hurdle to mass adoption of CNTs for biomedical applications was cytotoxicity [52–54]; however, advanced surface modifications have significantly improved the biocompatibility of these nanotubes [55,56]. Due to their biocompatibility and physical properties, CNTs are promising reinforcement materials and good conductive agents for cardiac [57–59] and neural [60,61] tissue engineering [62]. Biocompatibility of a purified suspension of CNTs interacting with mouse cardiomyocytes (H9c2) has shown that cell viability was unaffected by the presence of CNTs for the first 3 days (short-term biocompatibility). However, the long-term toxicity became apparent as apoptosis occurred after 3 days of cell culture in the presence of the nanotubes [63].

In other studies, pure CNTs were deposited on glass surfaces to investigate cardiomyocyte behavior. Martinelli *et al.* cultured neonatal rat cardiomyocytes on glass modified with MWCNTs (162 nm diameter). They discovered that the cardiomyocytes formed tight contacts and showed enhanced proliferation. After 2–3 days in culture, shorter action potentials of cardiomyocytes in the presence of MWCNTs were

reported [64]. In 2013, Martinelli and colleagues further demonstrated that deposition of 20–30 nm diameter MWCNTs on a glass substrate can promote cardiomyocyte growth and differentiation by altering gene expression and electrophysiological properties. MWCNTs (Fig. 3A.a) improved the electrophysiological characteristics of the cardiomyocytes, enhanced intracellular calcium signaling (Fig. 3Ab), and accelerated the maturation of functional syncytia. The expression of the Cx43 gene (Fig. 3A.c) was also increased; suggesting that CNTs may play a role in improving electrical conductivity by reinforcing electrical coupling between cardiomyocytes [65].

Liao *et al.* have demonstrated the production of MWCNT-incorporated polyvinyl alcohol (PVA)/chitosan nanofibers by electrospinning. The MWCNTs (30–70 nm diameter and 100–400 nm length) were incorporated in a blend of PVA and chitosan fibers (160 nm diameter). Incorporation of MWCNTs improved the protein adsorption ability of the nanofibers (Fig. 3B.a) and significantly promoted cell proliferation and adhesion (Fig. 3B.b and c) [66]. Wickham and colleagues have conjugated MWCNTs (7–15 nm diameter) to the surface of hydrophobic polycaprolactone (PCL) sheets and nanofiber meshes via thiophene. This group was able to increase the fiber's

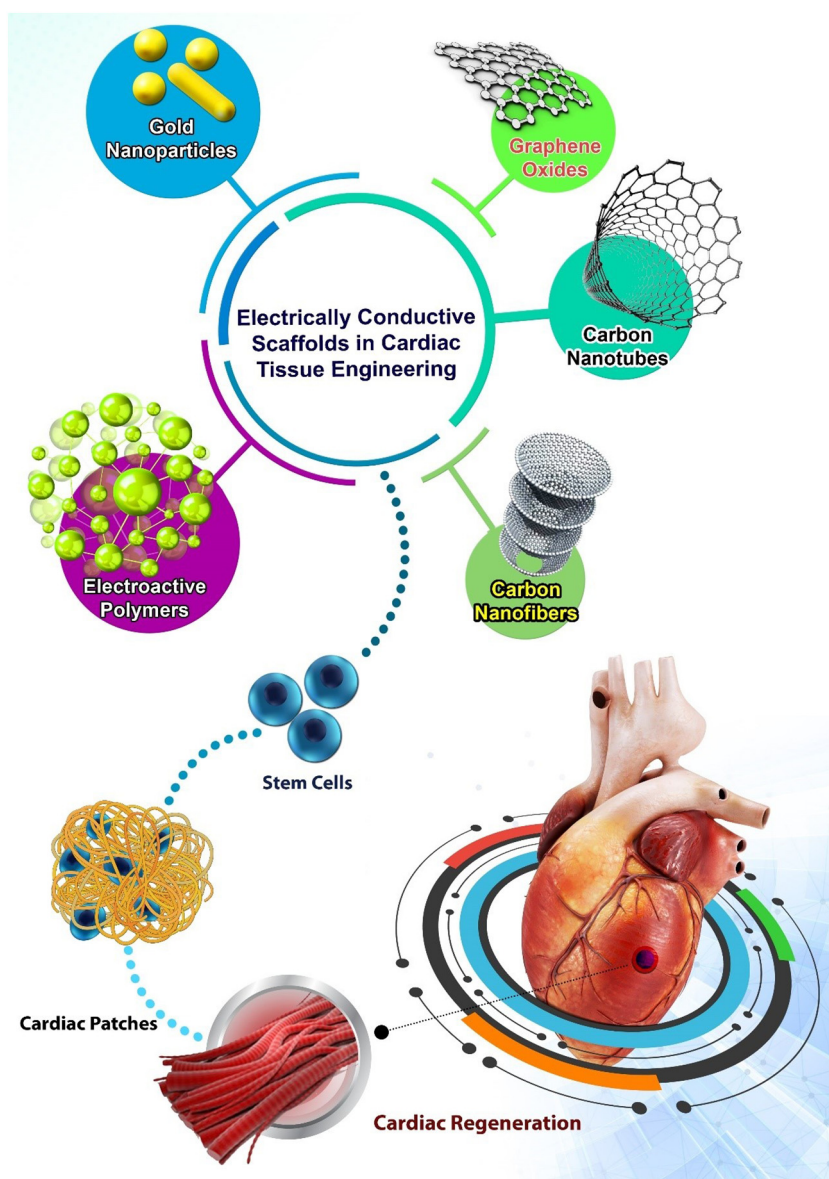


Fig. 2. Different categories of nanomaterials utilized for the production of electrically conductive cardiac tissue engineering scaffolds.

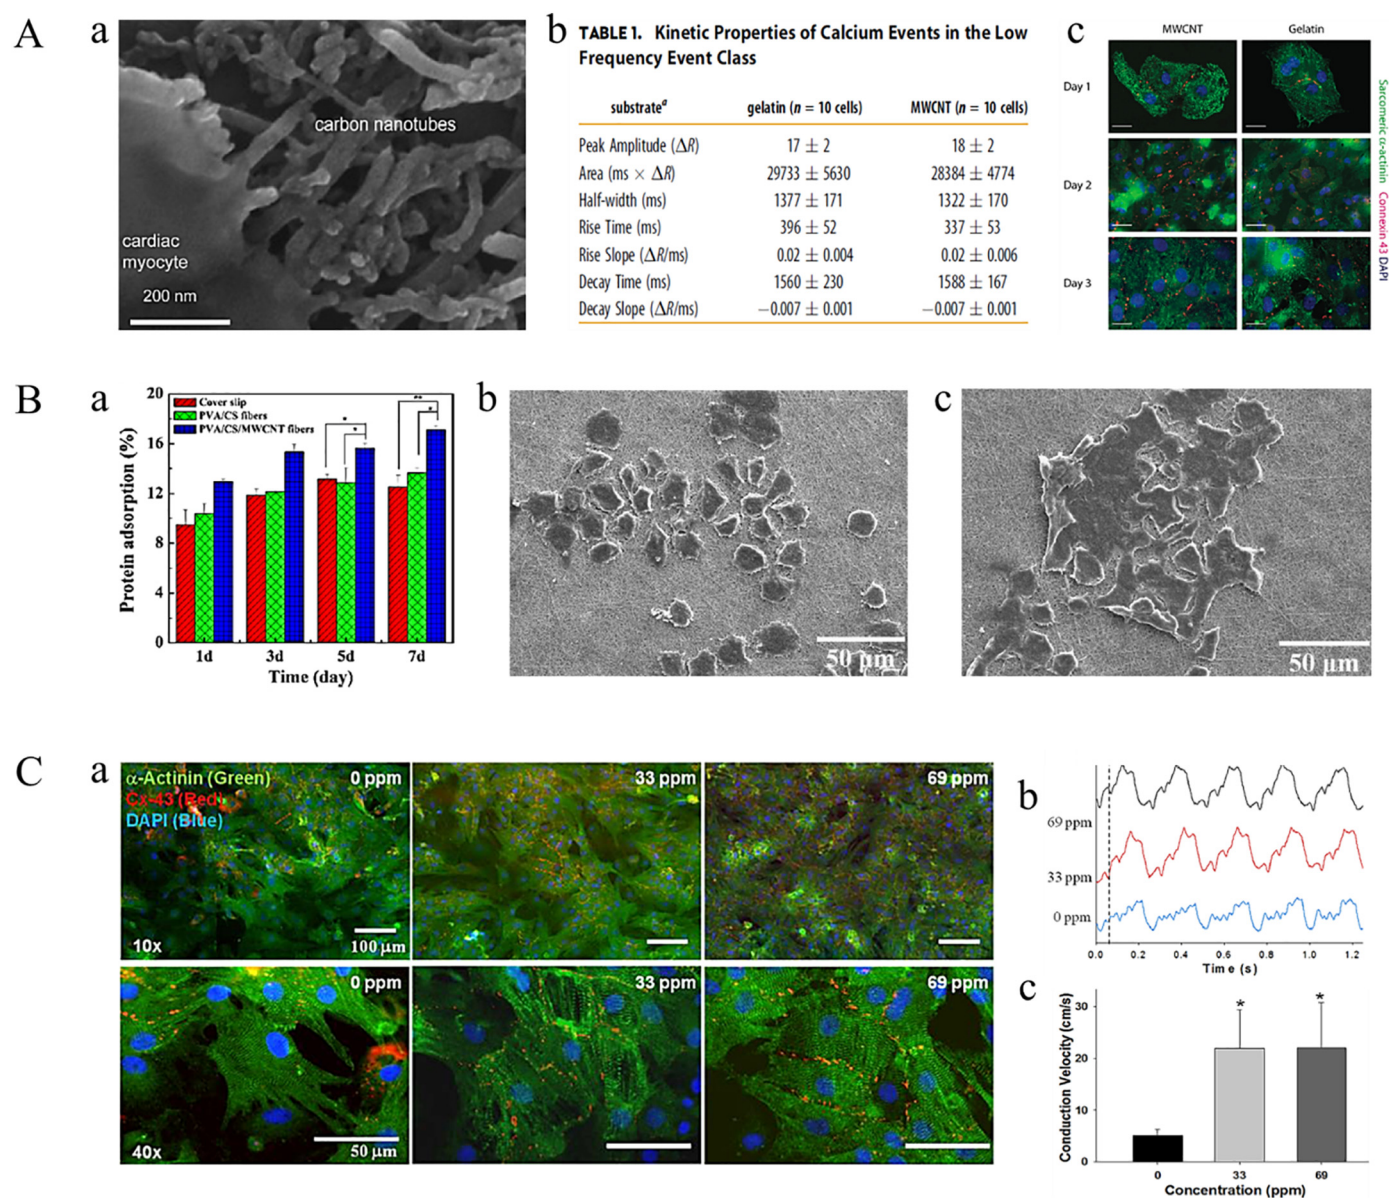


Fig. 3. Carbon-based nanomaterials in cardiac tissue engineering. (A) Instructing physiological growth and functionally mature syncytia using 20–30 nm MWCNTs. (a) Scanning electron microscopy (SEM) image of cardiac myocytes and MWCNT. (b) Reported data for the kinetic properties of calcium events of cells cultured on gelatin and MWCNTs. (c) Fluorescence images of cardiac myocytes, α -actinin (green), Cx43 (red) and nuclei (DAPI, blue). Distribution of Cx43 on the MWCNTs (left) and gelatin (right) scaffolds. Scale bars = 50 μ m. Reprinted from [65]. (B) Improved cellular response of cardiac cells on the MWCNT-incorporated PVA/chitosan scaffolds. (a) Incorporation of MWCNTs improved nanofiber protein adsorption. (b) PVA/chitosan nanofibrous mats without MWCNTs and (c) PVA/chitosan/MWCNTs nanofibrous mats. Reprinted from [66]. (C) CNT-chitosan scaffolds. (a) Fluorescence images of ventricular myocytes cultured on CNT-chitosan scaffolds. Cells stained for sarcomeres: α -actinin (green), gap junctions: Cx43 (red), and DNA. SWCNTs enhanced synchronous beating (b) and conduction velocities (c). Reprinted from [69].

mechanical strength without changing the mesh morphology. The addition of thiophene-conjugated CNTs to the PCL polymers also resulted in increased proliferation of cardiac progenitor cells (CPCs) [67]. Incorporation of CNTs in other materials, such as gelatin nanofibers and poly (glycerol sebacate) (PGS), notably enhanced the alignment, mechanical toughness, and electrical conductivity of fibers. The hybrid material resulted in strong and synchronized beating of cardiomyocytes. By incorporating the CNTs, the excitation threshold was 3.5 times lower and expression of Cx43 in cardiomyocytes was higher. In addition, the CNTs improved the scaffold's ability to mimic the anisotropic structure of the left ventricle [68].

Incorporation of CNTs in nanofibrous scaffolds has also been applied to cardiomyogenic differentiation of stem cells. In one study, researchers incorporated SWCNTs in electrospun PCL to fabricate an electrically conductive nanoscale scaffold. They employed electrical

stimulation to effectively differentiate human mesenchymal stem cells (hMSCs) into cardiomyocytes. The presence of CNTs resulted in elongated morphology and upregulation of cardiac markers such as Nkx-2.5, Cx43, GATA-4, and cardiac troponin T (CTT) [59]. Another study showed that MWCNT-doped PCL fibers can also enhance cardiac differentiation of hMSCs under electrical stimulation. The ionic resistance of doped fibers was measured through electrochemical impedance spectroscopy and the optimum amount of incorporated CNTs was chosen using conductivity measurements [70].

CNTs have also been integrated with hydrogels [71]. Hydrogels and soft tissues have similar mechanical and structural properties. Typical hydrogels, such as gelatin methacryloyl (GelMA), are also biodegradable. In 2013, Shin *et al.* created controllable three-dimensional (3D) biohybrid actuators for electrical stimulation of neonatal rat cardiomyocytes. They embedded aligned CNT (50–100 nm diameter)

forest microelectrode arrays into hydrogel plates of GelMA (50 μm thickness) to construct scaffolds with anisotropic electrical conductivity. The engineered tissues with the CNTs showed better cell organization, higher cell-to-cell coupling, and an increase in HL-1 cell maturation. Synchronized beating improved and significant reduction in excitation thresholds were observed. In the latter study, expression of troponin I and Cx43 was increased and no toxic effects were observed for 7 days [57]. In 2015, Elkhenany *et al.* incorporated 2 and 5 nm diameter MWCNTs in GelMA to fabricate electrically conductive scaffolds for investigating cardiac cell behavior under electrical stimulation (1 Hz, 5 V, 50 ms pulse width). They observed that overexpression of sarcomeric α -actinin and Cx43 led to improved cell behavior [72]. In another study, Pok *et al.* developed a scaffold containing subtoxic concentrations of SWCNTs (8 nm diameter \times 262 nm length) in a gelatin-chitosan hydrogel. Nanobridges of the SWCNTs between the cardiac cells led to enhanced expression of cardiac markers (Fig. 3C.a), synchronous beating (Fig. 3C.b), electrical coupling, and normal function of cardiomyocytes. Excitation conduction velocities (Fig. 3C.c) of engineered tissues were similar to that of the native myocardial tissue at 22 ± 9 cm/s [69]. Yu *et al.* incorporated carboxyl-functionalized MWCNTs into type I collagen hydrogels. They demonstrated that rhythmic contraction area of neonatal rat cardiomyocytes increased due to the addition of CNTs [73]. In another study, Ahadian *et al.* fabricated a series of moldable elastomeric scaffolds by incorporation of MWCNTs into a polyester called poly(octamethylene maleate (anhydride) 1,2,4-butanetricarboxylate). Their study demonstrated that scaffolds composed of 0.5% CNTs improved the excitation threshold in neonatal rat cardiomyocytes [74]. Also, Ho *et al.* fabricated PCL/MWCNT composite scaffolds for cardiac tissue engineering using 3D printing techniques [75]. This particular scaffold design offers selective treatments for complex cardiac tissues. In another attempt, Izadifar *et al.* fabricated hybrid cardiac patches by encapsulating human coronary artery endothelial cells in methacrylated collagen scaffolds with CNTs using a UV-integrated 3D bioprinting technique [76]. Additional researchers attempted to build on this success by designing hydrogels with the same function for more specific applications. In this regard, Roshanbinfar *et al.* fabricated an injectable, thermoresponsive, conductive scaffold by adding MWCNTs to pericardial matrix hydrogel. The functionalized MWCNTs with carbodihydrazide improved electrical and mechanical properties of the hydrogel, leading to an increase in cell proliferation and expression of Cx43 [77]. More recently, Cabiati *et al.* incorporated different concentrations of SWCNTs into gelatin-based genipin cross-linked scaffolds and observed overexpression of cardiac markers in cardiomyoblasts [78].

3.2. Carbon nanofibers

Carbon nanofibers (CNFs) are hollow cylinders with diameters between 50 and 500 nm and length on the order of microns. Because of their high aspect ratio (length/diameter greater than 100), they have been utilized for numerous applications. They have many unique physical and mechanical properties including a tensile strength of approximately 3 GPa, Young's modulus of 500 GPa, thermal conductivity of $1900 \text{ W m}^{-1} \text{ K}^{-1}$, electrical conductivity of approximately 10^3 S/cm [79,80], in addition to compatibility with organochemical modifications [81]. CNFs have cup-stacked or platelet structures that are less uniform compared to the hexagonal network of CNTs [82,83]. CNFs are fabricated using one of two methods: catalytic thermal chemical vapor deposition growth or electrospinning followed by heat treatment. CNF-reinforced polymer scaffolds can also be fabricated by dispersing CNFs in a polymer matrix, followed by either melt mixing or sonication in low viscosity solutions [83]. Several studies have mentioned applications of CNFs in neural [84,85], bone [86–89], muscle [90], and cardiac regeneration [91–93].

Stout *et al.* investigated cardiomyocyte function on poly(lactic-co-glycolic acid) (PLGA) and CNF composites. Their results revealed that

CNFs increased the conductivity and cytocompatibility of PLGA and promoted cardiomyocyte adhesion and proliferation. Also, the density of cardiomyocytes increased with the CNFs (up to 25:75 wt% PLGA: CNFs). The electrical conductivity of PLGA/CNF composites increased by adding CNFs of any diameter [91]. Meng *et al.* introduced injectable, biomimetic, electrically conductive scaffolds using CNFs, self-assembled rosette nanotubes (RNTs), and poly(2-hydroxyethyl methacrylate) (pHEMA) hydrogel for myocardial tissue engineering. As more CNFs and RNTs were incorporated into the pHEMA matrix, cardiomyocyte density in the hydrogel increased. Adding greater amounts of CNFs to the composites led to a decrease in tensile modulus and contact angle, but increased conductivity and surface roughness [92]. In order to mimic myocardial anisotropy, Asiri *et al.* created patterns (20 μm wide) of aligned CNFs (100 nm diameter) on the surface of PLGA (50:50 PGA:PLA weight ratio). The results showed that the CNF alignment increased the density of cardiomyocytes in the scaffold. Also, aligning the CNFs in the PLGA scaffold increased the longitudinal (vertical) conductivity to 0.1 S/m and decreased the horizontal (transverse) conductivity to 0.0025 S/m compared to a scaffold with randomly oriented fibers. These conductivities are similar to those of the natural heart tissue [93].

3.3. Graphene and its derivatives

Graphene is a freestanding, 2D active carbon allotrope. In graphene, the hexagonal aromatic structure is achieved by covalent bonds between each atom of carbon and three neighboring carbon atoms within the 2D crystal. The unique physical and electrical properties of graphene and its derivatives make it an ideal material for incorporation into composites to enhance desirable properties [94]. Moreover, high surface area of graphene facilitates the ability to load large quantities of bioactive compounds on its surface [95].

In vivo and *in vitro* biocompatibility of graphene and its derivatives has been reported in multiple studies [96,97]. Different approaches to improve biocompatibility such as oxidation, reduction, and functionalization, as well as controlling the size of graphene, have been demonstrated [95,98]. Wang *et al.* found that cardiogenic differentiation of human iPSCs could be improved by using superconductive sheets of graphene [99]. In a recent study, Smith *et al.* developed micro- and nano-patterned conductive hybrid scaffolds using graphene and polyethylene glycol (PEG). The anisotropic electrical conductivity and graphene-functionalized topography of these scaffolds led to an enhancement in myofibrils and sarcomeric structures in addition to an increase in electrical coupling of cardiac cells [100].

Graphene oxide (GO) is an oxidized form of graphene with colloidal stability that behaves as surfactant-like, amphiphilic sheets [101]. GO and reduced graphene oxide (rGO) have been used in combination with different materials as tissue engineering scaffolds. rGO has high conductivity and can also increase the hydrophobicity of scaffolds [102]. Additionally, the biocompatibility of rGO makes it a promising candidate for modifying bioprosthetic heart valves too [95,102].

In one study, Shin *et al.* incorporated GO into GelMA hydrogels for creating a cell-laden scaffold to investigate fibroblast behavior. Incorporation of GO significantly decreased the electrical impedance at low frequencies [103]. In another study, the same group used GO-based thin films and fabricated a 3D nano-structure through a layer-by-layer (LbL) technique. The GO sheets were coated with poly-L-lysine (PLL). Neonatal rat ventricular cardiomyocytes between the PLL and the GO under electrical stimulation showed spontaneous beating, cardiac cell organization, cell maturation, and cell-to-cell electrical coupling [104]. Also, the incorporation of rGO into GelMA hydrogels enhanced electrical conductivity and mechanical properties of the material. The modified GelMA improved cardiomyocyte viability, proliferation, and maturation in addition to inducing increased spontaneous beating rates [105]. Incorporation of graphene-based nanomaterials into hydrogels can improve both mechanical and electrical properties of hydrogels. These

Table 1

Carbon-based nanomaterials in cardiac tissue engineering.

Material	Electrical cues	Scaffold	Cell	Results	Limitations	Year	Ref.
Aqueous SWCNTs	Not mentioned	Pure CNTs/SWCNTs	H9c2	<ul style="list-style-type: none"> - No short-term toxicity - Biocompatible 	Cell death due to physical interactions with SWCNTs	2005	[63]
Precipitated MWCNTs on glass surface	More negative resting and action potential duration after 2–3 days Significant growth in resting membrane potential	Pure MWCNTs (162 nm) deposited on glass	NRVC	Improved viability and proliferation	Not suitability of glass surfaces for implantation	2012	[64]
		Pure MWCNTs (20–30 nm) deposited on glass	NRVC	<ul style="list-style-type: none"> - Enhanced expression of terminal differentiation gene - Functional gap junctions were formed in syncytia 		2013	[65]
CNFs incorporated in nanofibers	Increased conductivity irrespective of CNFs diameter	PLGA/CNFs (100 and 200 nm)	Human cardiomyocytes	Improved cardiomyocytes proliferation and density using 200 nm CNFs	Potential toxicity of CNFs during degradation	2011	[91]
	CNF conductivity	pHEMA /CNFs (100 nm) / RNTs (inner/outer diameters of 1.1/3.5 nm)	Human cardiomyocytes	Increased cardiomyocytes density		2012	[92]
	Obtaining electrical resistance in horizontal and vertical direction with four-point probe method close to natural heart tissue	PLGA (100 nm)/aligned CNFs	Cardiomyocytes	Improved anisotropic mechanical and electrical properties		2014	[93]
CNTs incorporated in nanofibers	Not mentioned	PVA/Chitosan (157 nm) / MWCNTs (70–30 nm × 100–400 nm)	L929	Increased cell proliferation	<ul style="list-style-type: none"> - Potential toxicity of CNTs during degradation - May require additional manufacturing processes to develop 3D scaffolds - Low control on CNT dispersion in naofibers 	2011	[66]
	Not mentioned	PCL/thiophene/MWCNTs (15–7 nm × 2 μm)	CPCs	<ul style="list-style-type: none"> - CPCs induced to survive and differentiate - Proliferation was higher on the PCL/-thiophene-CNT meshes 		2014	[67]
	Electrical field stimulation (biphasic square wave 5ms pulse / 0–7 volt / 1–3 Hz frequency)	PGS/gelatin (167 nm)/MWCNTs (30 nm diameter 20–50 nm length)	Cardiomyocytes	<ul style="list-style-type: none"> - Spontaneous and synchronous beating behavior were observed - Resembling the myocardium anisotropic structure. - Contractile properties of the cardiomyocytes were significantly improved 		2014	[68]
	Electrically stimulation (current of 0.15 V/cm and frequency of 1 Hz) for 14 day	SWCNTs	hMSCs	<ul style="list-style-type: none"> - Upregulation of cardiac markers - 40 fold increase in cardiac myosin heavy chain - Upregulation of Nkx-2.5, GATA-4, CTT, and Cx43 		2012	[59]
	Extrinsic electrically stimulation (current of 500 V/m, 5 ms duration, frequency of 1 Hz) for 4 days	PCL/MWCNTs	hMSCs	<ul style="list-style-type: none"> - Cardiac cardiomyogenic differentiation of hMSCs was promoted - Elongated cell morphology - Elevated expression of cardiac troponin T (cTnT), Nkx-2.5, and myosin heavy chain 		2013	[70]
CNTs nanofibers	External electric field (1 V/cm at	GelMA/MWCNTs (50–100	NRVC			2013	[57]

Table 1 (continued)

Material	Electrical cues	Scaffold	Cell	Results	Limitations	Year	Ref.
incorporated in hydrogels/polymers	1, 2, and 3 Hz)	nm diameter)		<ul style="list-style-type: none"> - Improved cell-cell coupling - Homogeneous cell organization and Cx43 distribution - Partial uniaxial alignment of sarcomeric structures 	<ul style="list-style-type: none"> - Difficult to incorporate an ideal balance of materials to create the proper microenvironment - Low amounts of CNTs can be dispersed in hydrogels/polymers - Increase in electrical conductivity of scaffolds is not sufficient 		
	Electrical stimulation square wave 1 Hz at 5 V (50 ms pulse width) Conductivity of aligned CNTs was 12.1 S/cm	GelMA/MWCNTs (2 and 5 nm)	Cardiac cells	<ul style="list-style-type: none"> - Homogeneous cell organization - Overexpression of sarcomeric α-actinin and Cx43 		2015	[106]
	Not mentioned	Collagen/chitosan/SWCNTs (0.8 nm \times 262 nm length)	Cardiomyocytes	Enhanced electrical coupling, synchronous beating, and cardiomyocytes function.		2014	[69]
	Not mentioned	Type I collagen, MWCNTs (30 \pm 15 nm \times 5–20 μ m)	Neonatal rat cardiomyocytes	Improved cardiac cell functions		2017	[73]
	Not mentioned	MWCNTs (40–90 nm \times 10–20 μ m), poly (octamethylene maleate (anhydride) 1,2,4-butanetricarboxylate)	Neonatal rat cardiomyocytes	Improved maturity and excitation threshold		2017	[74]
	PCL with 3% CNTs (Conductivity of 2.2×10^{-7} S/cm) PCL with 5% CNT (Conductivity of 1.2×10^{-6} S/cm) The electrical conductivity of scaffold was 0.015 S/cm	PCL, MWCNTs (20–30 nm \times 10–30 μ m)	Rat H9c2 cells	Myoblast cells attached to the scaffolds in a healthy condition for 4 days.		2016	[75]
		MWCNTs functionalized with carbodihydrazide (\approx 166 nm), pericardial matrix hydrogel	HL-1 cardiomyocytes	<ul style="list-style-type: none"> - Increased expression Cx43 - Improved beating - Increased cellular viability 		2017	[77]
	Not mentioned	SWCNTs (average diameter of 50 nm), gelatin	Rat H9c2 cells	Increased proliferation, differentiation, and electrical conductivity of cells		2017	[78]

nanomaterials can also provide nanotopography similar to natural *in vivo* environments, resulting in better cell-to-cell signaling, and ameliorating signal propagation – all of which are essential parameters in cardiac tissue engineering [95]. Table 1 gives a summary of carbon-based nanomaterials that have been applied to cardiac tissue engineering.

4. Gold nanomaterials

Gold nanoparticles (AuNPs) have been studied extensively for many biological and medical applications due to their controlled geometrical, optical, and surface chemical properties [107]. Low cytotoxicity and biocompatibility of AuNPs are demonstrated in several studies [108,109]. AuNPs can be synthesized in different shapes including nanospheres, nanorods [110,111], tripods [112], tetrapods [112], nanocubes [113], and nanocages [114]. They also can be transformed into nanofibers, thin films, or nanoshells. Unique specific absorbance spectra have been reported corresponding to different shapes of AuNPs. A variety of geometries can be used for medical applications including diagnosis, sensing, molecular imaging, and stem cell tracking. Additionally, the nanoparticles can be used to enhance electrical conductivity of nanocomposites. High electrical conductivity, acceptable biocompatibility, ease of surface modification, nanotopography, and innate optic properties make AuNPs a desirable nanostructure for cardiac scaffolds.


Shevach *et al.* have deposited AuNPs on decellularized omental matrix in order to make an electrically conductive scaffold for cardiac tissue

engineering (Fig. 4A.a). Cardiac cells showed elongated and aligned morphology and increased Cx43 expression. These hybrid AuNP/omental patches demonstrated increased contraction force (Fig. 4A.b), lower excitation threshold, and boosted propagation of calcium signals [115].


In another study, Fleischer *et al.* integrated AuNPs into PCL electrospun fibers to fabricate an electroconductive nanocomposite scaffold for myocardium tissue engineering. Cardiomyocytes in the presence of AuNPs, exhibited aligned and elongated morphology, stronger contraction forces, and lower excitation thresholds in presence of electrical fields [116]. Shevach *et al.* deposited AuNPs (thickness of 2, 4, and 14 nm) on the surface of synthetic PCL-gelatin matrix nanofibers (250 nm diameter). This engineered hybrid nanocomposite enhanced cardiomyocyte elongation, alignment, cardiac sarcomeric α -actinin expression, and resulted in higher cell contraction amplitudes and rates (Fig. 4B) [117].

Cardiomyogenic differentiation of stem cells has also been studied in AuNP-loaded nanofibrous scaffolds. For example, Ravichandran *et al.* incorporated AuNPs into bovine serum albumin (BSA)/PVA hybrid nanofibers. By culturing hMSCs on an AuNP-loaded conductive nanofibrous scaffold with 5-azacytidine pre-treatment, cardiomyogenic differentiation of hMSCs was remarkably enhanced (Fig. 4C) [118]. In another study, Sridhar *et al.* incorporated different materials such as AuNPs, vitamin B₁₂, silk fibroin, and aloe vera in a series of PCL scaffolds in which they co-cultured cardiomyocytes and MSCs. The AuNP-blended scaffolds enhanced proliferation and cardiomyogenic differentiation of MSCs. Functionalized biomaterials with AuNPs showed high mechanical


A Hybrid AuNPs/omental scaffolds

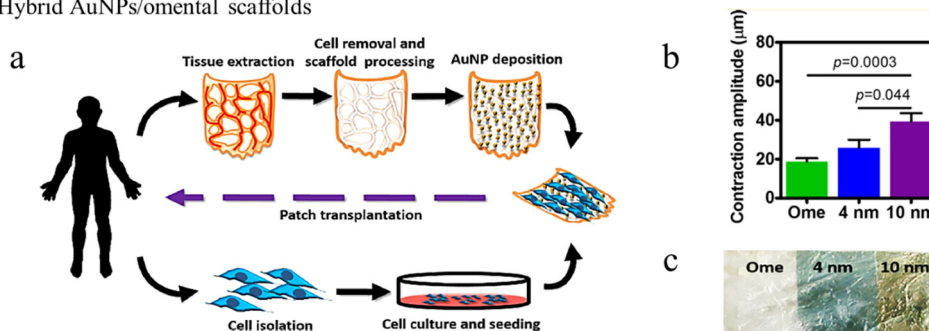

B Evaporated AuNPs on PCL/gelatin nanofibers

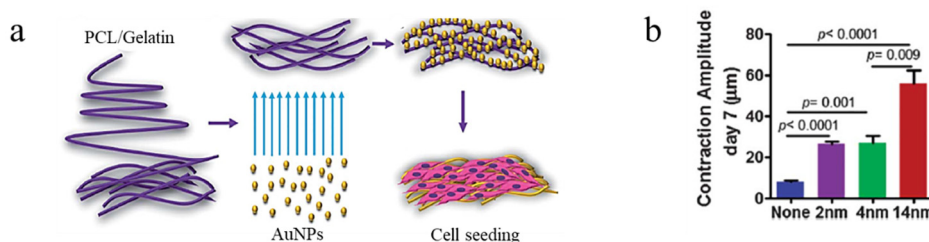

C Incorporation AuNPs into BSA/PVA hybrid nanofibers

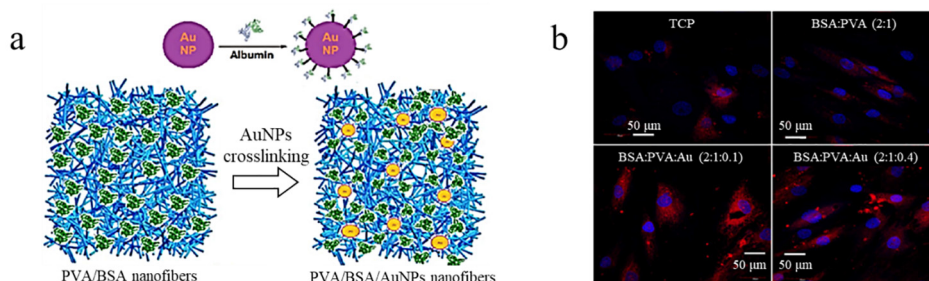

D Blended 3D nanocomposite complex with electronics

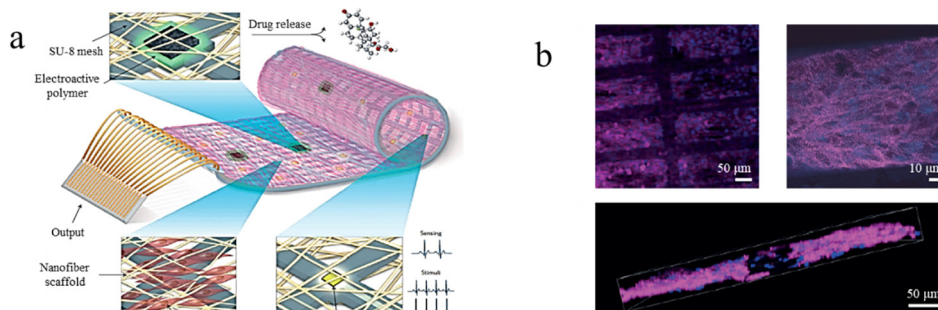


Fig. 4. Gold nanomaterials in cardiac tissue engineering. (A) Modifying electrical properties of omental matrix using AuNPs. (a) Decellularized omental matrix was decorated with AuNPs using an e-beam evaporator. Cells were isolated from the same patient, placed on the scaffold for a personalized cardiac patch. (b) These hybrid scaffolds led to stronger contraction forces generated by cardiomyocytes. (c) Deposition of AuNPs, with thicknesses of 4 and 10 nm on the scaffold's fibers, caused a color change in the scaffold. Reprinted from [115]. (B) Increasing the matrix conductivity of microporous scaffolds by incorporating AuNPs. (a) AuNPs (2, 4, and 14 nm) were evaporated on the surface of PCL-gelatin nanofibers (250 nm diameter). (b) Cardiac cells seeded in these scaffolds showed enhanced contraction amplitude and rate. Reprinted from [117]. (C) AuNPs incorporated into BSA/PVA hybrid nanofibers remarkably enhanced cardiomyogenic differentiation of hMSCs. (a) The mechanism of crosslinking of AuNPs in bovine serum albumin (green) and AuNPs (yellow). (b) Immunocytochemical results indicated gap junction protein expression, Cx43 (red), by differentiated contractile MSCs, DAPI: blue. Reprinted from [118]. (D) (a) A blended 3D nanocomposite complex with embedded electronics for online monitoring of engineered cardiac patches. (b) Confocal microscope images of the assembled cardiac tissue within the biomaterial–electronics hybrid. Sarcomeric actinin is pink, nuclei are blue. Reprinted from [128].

strength and resulted in better contractile characteristics for cardiac cells [119].

Hydrogels are also good candidates for integrating gold nanocomposites to create 3D scaffolds. You *et al.* incorporated AuNPs homogeneously

into a thiol-HEMA/HEMA hybrid hydrogel to mimic physiological properties of natural myocardial ECM. Young's modulus of the composite gel was closer to the *in vivo* myocardium in comparison with naked polyaniline (PANI) and polypyrrole (PPy). The AuNPs enhanced

Table 2

Examples of the use of gold nanomaterials in cardiac tissue engineering.

Material	Electrical cues	Scaffold	Cells	Results	Limitations	Year	Ref.
Decellularized matrices + AuNPs	Electrical stimulation	AuNPs (4 and 10 nm)/decellularized omental matrices	Cardiac cells	<ul style="list-style-type: none"> - Elongated and aligned cell morphology - More Cx43 expression - Stronger contraction force - Faster calcium transient 	<ul style="list-style-type: none"> - AuNPs may dissociate from the scaffold <i>in vivo</i> - Non-degradation of AuNPs - Mismatch between mechanical properties of decellularized ECM and AuNPs 	2014	[115]
Fibrous scaffold + AuNPs	External electrical field	Gold (film)/PCL	NRVC	<ul style="list-style-type: none"> - Significantly higher aspect ratio and stronger contraction forces - Reaction to significantly lower electrical fields 	<ul style="list-style-type: none"> - Non-degradation of AuNPs <i>in vivo</i> - Los dispersion of AuNPs in scaffolds 	2014	[116]
	Not mentioned	AuNPs (2, 4 and 14 nm)/PCL/gelatin (250 nm)	NRVC	<ul style="list-style-type: none"> - Enhanced elongation and alignment, more cardiac sarcomeric α-actinin expression, higher contraction amplitudes and rates 		2013	[117]
	Not mentioned	BSA/PVA/AuNPs	hMSCs	<ul style="list-style-type: none"> - Cardiomyogenic differentiation - Multinucleated morphology - Improved cardiac protein expression (α-actinin, troponin T and Cx43) 		2014	[118]
	Not mentioned	PCL/Vit B12/Aloe Vera/Silk fibroin/AuNPs (16nm)	hMSCs	<ul style="list-style-type: none"> - Proliferation and cardiogenic differentiation were enhanced 		2015	[119]
Hydrogel scaffold + AuNPs	Scaffold conductivity: 15.3 ± 0.8 S/m	AuNPs (8.1 ± 0.9 nm and 4.4 ± 0.3 nm)/thiol-HEMA	NRVC	<ul style="list-style-type: none"> - Cx43 expression was increased 	AuNPs may interfere with hydrogel crosslinking	2011	[99]
	Electrical stimulation (2mA rectangular pulses, 2 ms, 1 Hz, 5 V/cm) for 5 days						
	Electrical conductivity of scaffold was close to the native myocardium 0.13 S/m	Chitosan/AuNPs (7.24 nm)	hMSCs	<ul style="list-style-type: none"> - Scaffolds supported viability, metabolism, migration and proliferation of hMSCs - Significantly increased expression of α-myosin heavy chain (α-MHC) and Nkx-2.5 		2016	[102]
	Not mentioned	GelMA hydrogel, gold nanorods (average aspect ratio of $3.15, 16 \pm 2/53 \pm 4$ nm width and length)	Cardiomyocytes	<ul style="list-style-type: none"> - High cell retention - Improved cytoskeleton organization - Enhanced expression of cardiac markers 		2016	[104]
	Not mentioned	Collagen and AuNPs	Cardiac muscle cells	<ul style="list-style-type: none"> - AuNPs regulated the assembly of intercalated discs via the $\beta 1$ integrin-mediated ILK/p-AKT/-GATA4 pathway 		2016	[105]
Gold nanowire	Scaffolds showed low impedance at high frequencies (10 kHz)	Gold nanorods ($34 \text{ nm} \times 25 \text{ nm}$ wide), GelMA	Neonatal rat ventricular cardiomyocytes	<ul style="list-style-type: none"> - Improved the electrical propagation between cardiac cells 		2017	[106]
	Electrical stimulation: square pulse (1 V/mm amplitude, 2 ms pulse duration, frequency of 1 Hz) for 15 min.	Alginate/gold nanowire (30 nm)	Cardiac cells	<ul style="list-style-type: none"> - Thicker and aligned engineered tissues - Expression of Cx43 increased 	Gold nanowires can be entered the cell membrane and cause cytotoxicity	2011	[101]
		Castor oil based polyurethane/gold	H9c2	<ul style="list-style-type: none"> - Increased cell confluency - Up-regulation of myocardial functional gene expression: Nkx-2.5, atrial natriuretic peptide and natriuretic peptide precursor B 		2016	[103]
New Devices	Electronic devices that can control cell/tissue function	Gold used as electrodes		<ul style="list-style-type: none"> - Flexible cardiac patch, which is freestanding in cardiac 3D scaffolds 	Proving safety and efficacy at low voltages is essential	2016	[107]

expression of Cx43 in neonatal rat ventricular cardiomyocytes (NRVC) in the hybrid scaffolds [120]. Naseri *et al.* incorporated silica-gold core-shell spheres into PCL composite films. The electrical conductivity of the scaffold was 1.51 S/cm. The particles were composed of 20 nm gold nano-shells covering silica microspheres (1.1 μm diameter) [121].

Dvir *et al.* demonstrated that the incorporation of gold nanowires (30 nm diameter) with alginate could upregulate electrical and mechanical coupling proteins (like Cx43) to make better 3D cardiac patches

[122]. Cardiomyogenic differentiation of stem cells has also been investigated in AuNP-incorporated hydrogels. In one study, Baei and colleagues dispersed AuNPs into thermosensitive chitosan matrices to make a conductive polymeric scaffold for cell stimulation. Their results revealed a comparable level of viability, metabolism, migration, and proliferation of bone marrow-derived MSCs and relatively high expression of cardiac-specific markers compared to chitosan hydrogel scaffolds without AuNPs. Also, electrical conductivity close to that of the native myocardium

(around 0.13 S/m) was observed [123]. Ganji *et al.* incorporated gold nanowire/nanotubes into porous polyurethane and fabricated biodegradable nanocomposites. Continuous electrical stimulation of H9c2 cells cultured on these scaffolds facilitated increased confluency and myocardial expression of Nkx-2.5, atrial natriuretic peptide, and natriuretic peptide precursor [124]. In another example, Navaei *et al.* fabricated a new class of scaffolds by incorporating gold nanorods into GelMA hydrogels. These scaffolds raised the expression of cardiac-specific markers including troponin I and sarcomeric actinin from neonatal rat ventricular cardiomyocytes [125]. In another study, Li *et al.* developed a hybrid scaffold from natural collagen and AuNPs. They found that the presence of AuNPs regulated the assembly of intercalated discs in cardiomyocytes via the $\beta 1$ integrin-mediated ILK/p-AKT/GATA4 pathway [126]. To accommodate the use of new manufacturing technologies such as 3D printing, Zhu *et al.* developed a conductive bioink by incorporating gold nanorods into GelMA. These bioprinted constructs increased synchronized contraction and electrical propagation between cardiomyocytes [127].

Feiner *et al.* blended 3D nanocomposites with a complex electronic mesh device for online monitoring of engineered cardiac tissues. In order to sense the release of biomolecules and the electrical activity in cells and tissues, a gold electrode-based device was integrated with the electrospun scaffolds (Fig. 4D) [128]. Table 2 shows different scaffolds incorporating AuNPs that have been fabricated for cardiac tissue engineering applications.

5. Electroactive polymers

Electroactive polymers (EAPs) are smart materials with controllable conductive properties suitable for fabrication of electrically conductive scaffolds. Their chemical, electrical, and physical properties can be tuned by incorporating antibodies, enzymes, and other biological components to meet the requirements of a specific application. Chemical and electrochemical synthesis are two main methods of manufacturing conductive polymers [27]. Many polymers are not conductive; therefore, they require a process called “doping” to transform into a conductive material. PPy, PANI, and polythiophene (PTh) are some important EAPs, which have potential applications in cardiac tissue engineering.

5.1. Polypyrrole

PPy is one of the best-known conductive polymers. Stimulus-responsive properties, *in vitro* and *in vivo* biocompatibility [132], appropriate chemical stability, large specific surface area, and aptitude for surface modifications to incorporate bioactive molecules [27] make PPy an excellent candidate as a scaffold for cardiac tissue engineering. In 2007, Nishizawa *et al.* electrochemically deposited PPy films onto polyimide microelectrodes. Primary cardiomyocytes formed sheets on these electrodes and displayed synchronized beating upon non-invasive stimulation [133]. Spearman *et al.* grew PPy films within PCL (treated with sodium hydroxide) films in order to form functional sheets of cardiac cells. Cardiomyocytes demonstrated an increase in Cx43 expression, faster calcium transfer, and lower calcium transient durations. Surface resistivity of the PCL/PPy film was $1.0 \pm 0.4 \text{ k}\Omega \text{ cm}$ [134]. In order to optimize PPy biomaterials for CPCs, Puckert *et al.* investigated the effect of surface properties on the viability of CPCs. The effect of different dopants on electroactivity of PPy was investigated using cyclic voltammetry (CV). The group established fabrication parameters to control the surface energy, morphology, and roughness of the materials [135].

In 2015, Gelmi and colleagues deposited chlorine doped-PPy on electrospun PLGA fibers to make 3D and electrically conductive scaffolds. Their results confirmed biocompatibility of these scaffolds using cardiac progenitor cells and iPSCs [136]. Kai *et al.* demonstrated that electrospun PPy/PCL gelatin nanofibers could not only improve the overall function of cardiomyocytes, but also increase the expression of cardiac-functional proteins (α -actinin, troponin T, and Cx43). They also observed that incremental increases of PPy concentration could decrease nanofiber diameter and increase the tensile modulus of the

scaffolds. The nanofibers had an electrical conductivity between 0.01 and 0.37 mS/cm [137].

In 2015, Mihic *et al.* conjugated PPy to chitosan and developed a semi-conductive hydrogel (Fig. 5A.a). *In vitro* studies demonstrated faster calcium transfer and lower calcium transient durations for cardiomyocytes in the conductive hydrogel (Fig. 5A.b and d). By increasing the amount of PPy in PPy-chitosan hydrogels, the electrical conductivity of gels was increased. A decrease in the QRS (one of three main waveforms in heart electrocardiograms) interval, an increase in the transverse activation velocity, and significantly higher action potential amplitudes were observed for the cells in the PPy-chitosan gels compared to un-grafted chitosan [129]. Recently, Wang *et al.* fabricated a conductive cryogel by integrating PPy nanoparticles, GelMA, and PEG diacrylate (PEGDA) using a mussel-inspired dopamine crosslinker. *In vitro* and *in vivo* studies showed that migration of PPy nanoparticles from the scaffold to cardiomyocytes resulted in excellent synchronous contraction and a reduction in infarct size [138]. In another study, Gelmi *et al.* coated PLGA fibers with PPy and made a biocompatible and electroactive scaffold for cardiogenic differentiation of human iPSCs under electromechanical stimulation [139].

5.2. Polyaniline

PANI is the oxidative polymeric product of aniline [140] and exists in different systems according to its oxidation level. Pernigraniline (fully oxidized base), emeraldine (half-oxidized base), and leucoemeraldine (reduced base) are some forms of PANI. Emeraldine is conductive and is the most stable form. PANIs are not only easy to synthesize, but also have good stability. Moreover, they are cost efficient and able to be either electrically conductive or resistant [27]. Many synthesis methods for nano/micro-fabrication of PANI have also been published [141]. However, PANI is not suitable for many biological applications as it is inflexible and biodegradable, making it difficult to integrate into soft cardiac tissue. Chronic inflammation in implanted tissues was reported due to PANI [142,143]. However, some studies have been conducted on cellular interactions with PANI in nerve, muscle, and cardiac tissue engineering [144–146].

In 2006, Bidez *et al.* investigated adhesion, growth, and proliferation of cardiac H9c2 myoblasts cultured on PANI films for 200 h. In the first 100 h, the doubling time increased. Also, the results showed that this scaffold maintained its conductivity for the first 100 h in the physiological environment. However, its conductivity gradually decreased over time [147].

Scientists have combined PANI with different biological materials to enhance its biocompatibility. For example, Li and his colleagues produced a nanofibrous blend based on co-electrospinning PANI and gelatin. The PANI was doped with camphorsulfonic acid to form emeraldine PANI. Their results revealed that increasing the amount of PANI in the mixture led to reduced fiber diameter and increased tensile modulus. This biocompatible scaffold supported attachment, migration, and proliferation of cardiac myoblasts. Also, the conductivity of pure gelatin was determined to be 0.005 S/cm; however, the conductivity increased about four-fold by increasing the PANI concentration [148]. Fernandes *et al.* modified PANI nanofibrous scaffolds (69–80 nm diameter) with hyper-branched PLL dendrimers (4.5 nm diameter) [149]. Neonatal rat heart cells showed high biocompatibility and better proliferation with electrical stimulation in the scaffolds. To improve the hydrophilic properties of PANI nanotubes, Moura *et al.* functionalized them with highly hydrophilic polyglycerol dendrimers (80–180 nm diameter). This modification allowed the scaffold to support cardiac cell proliferation and adhesion [150].

Hsiao *et al.* synthesized PANI-PLGA aligned fibers to develop a 3D environment for synchronous beating of cardiomyocytes (Fig. 5B.a and b). They showed that this scaffold increased the expression of gap junction protein (Cx43) and troponin T (Fig. 5B.c). The cardiomyocytes also formed isolated cell clusters and beat synchronously. The HCl-doped

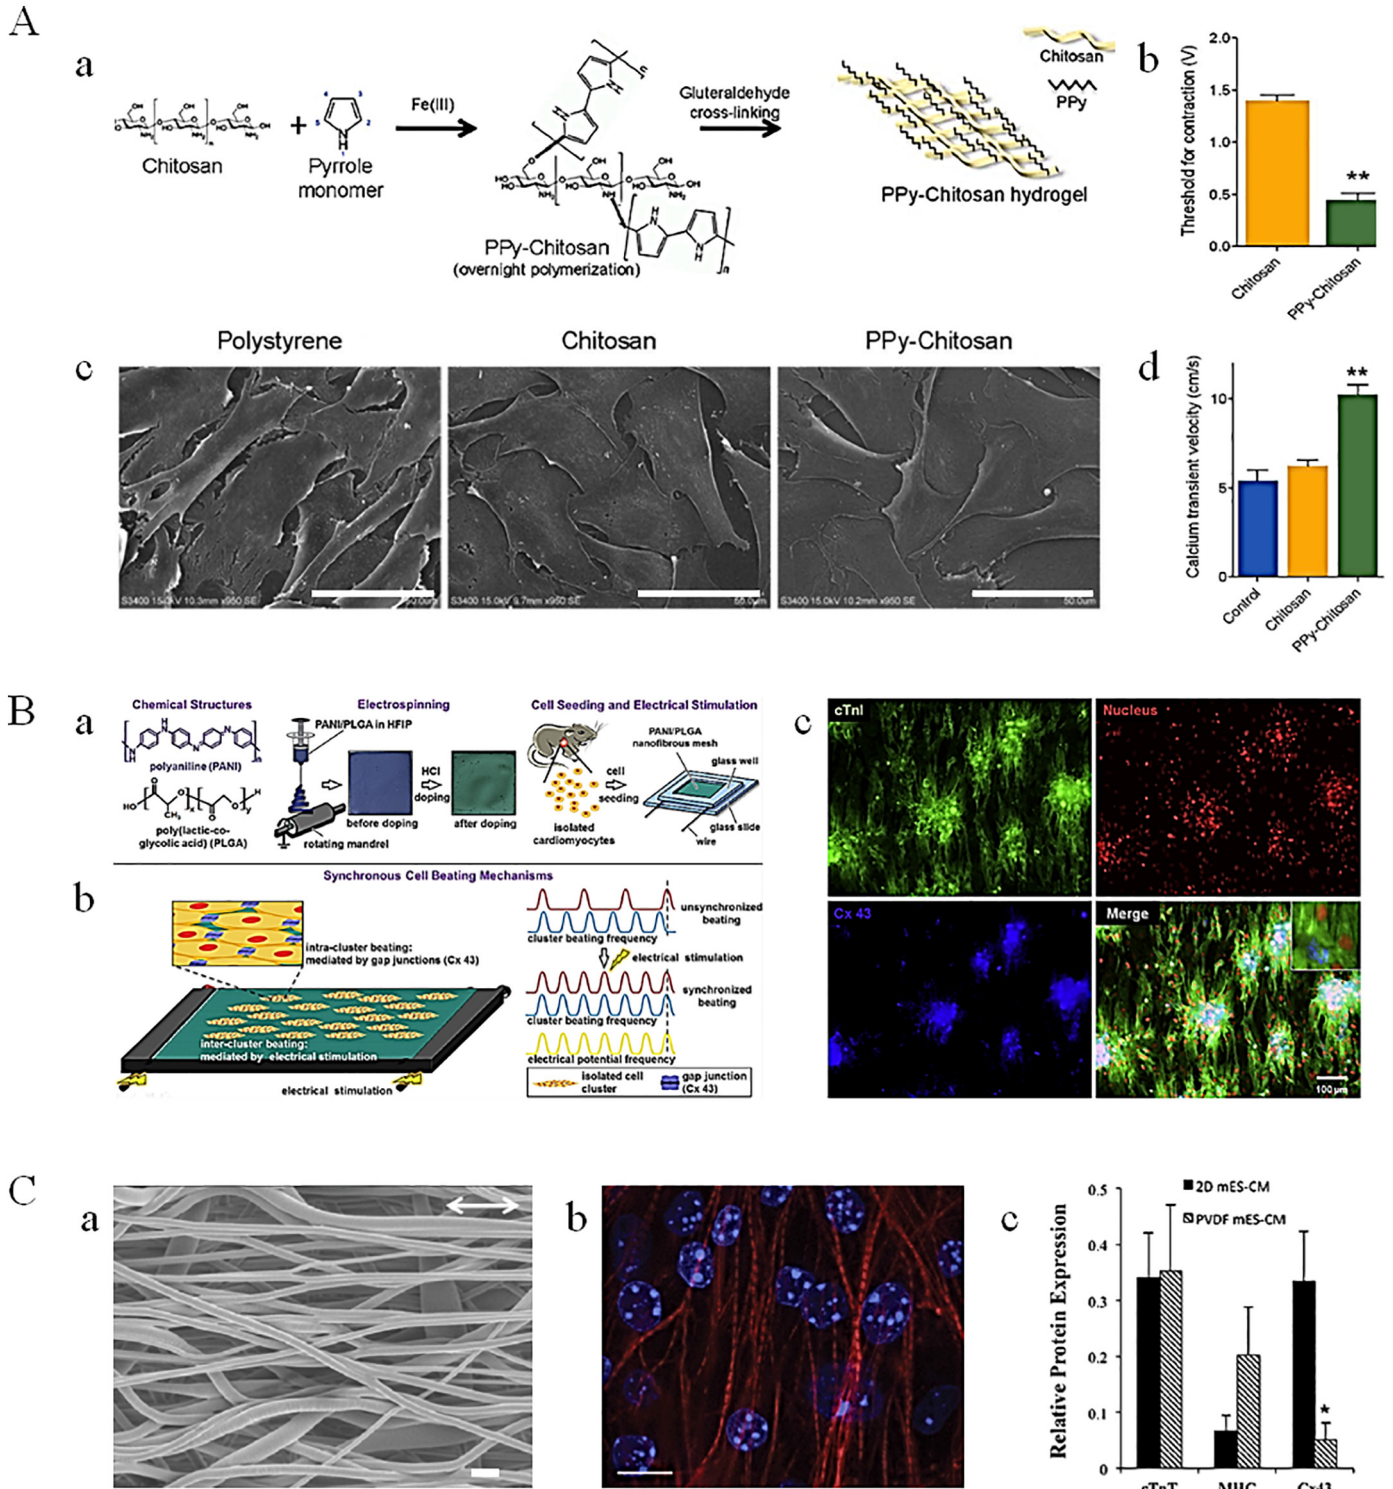


Fig. 5. EAPs in cardiac tissue engineering. (A) PPY conjugated to chitosan formed a semi-conductive hydrogel to enhance Cx43 expression, faster calcium transfer, and lower calcium transient durations for cardiomyocytes. (a) PPY monomers grafting and cross-linking into a hydrogel. (b) Contraction threshold voltage was measured using anion-contact stimulation of a single skeletal muscle. PPY-chitosan had a lower threshold voltage than chitosan. (c) A normal morphology was observed in the SEM images of rat smooth muscle cells which were plated on polystyrene, chitosan, or PPY-chitosan. Scale bars = 500 μm . (d) Faster transient velocity was observed for calcium in rat neonatal cardiomyocytes which were plated on PPY-chitosan. Reprinted from [129]. (B) PANI-PLGA aligned fibers developed a 3D environment for synchronous beating of cardiomyocytes and increasing expression of gap junction proteins. (a, b) Synthesis, seeding, and stimulation of the PANI/PLGA nanofibrous mesh for synchronous cell beating. (c) Fluorescence images of neonatal rat cardiomyocytes cultured on meshes (cardiac troponin I is green, Cx43 is blue, and nuclei are red). Reprinted from [130]. Scale bar = 100 μm . (C) Cardiomyocytes adhered well to piezoelectric scaffolds made by electrospinning PVDF and PVDF-TrFE. (a) SEM image of a PVDF-TrFE scaffold with aligned fibers. Scale bar is 2 μm . (b) Aligned actin filaments with well-placed sarcomeres. F-actin is stained red and DAPI-stained nuclei are blue. Scale bar = 10 μm . (c) Expression of cTnT, MHC, and Cx43 in cardiomyocytes cultured on PVDF-TrFE scaffolds compared to 2D cell culture. Reprinted from [131].

Table 3

Summary of the electroactive polymer scaffolds used in cardiac tissue engineering.

Material	Electrical properties	Scaffold	Cell	Results	Year	Ref.
Polypyrrole	Surface capacity of PPY thin films on the electrode substrate: 5.8 C/cm ²	Pt microelectrodes on polyimide (PI) surface/PPy film	Primary cardiomyocytes	- Adhesive strength of PPY film was enhanced - Cells showed synchronized beating upon stimulation	2007	[133]
	Surface resistivity PCL/PPy: 1.00 ± 0.40 kΩ.cm	PCL films/PPy	HL-1	- Functional cardiac cell sheets formed - Increased in Cx43 expression - Faster calcium transfer	2015	[134]
	Dopants enhanced electroactivity of PPY though as measured by cyclic voltammetry (CV)	PPy/different dopants CS/PTS/DBS	CPCs	- Lower calcium transient durations	2016	[135]
	PPy increased the capacitance of scaffolds	Electrospun PLGA fibers/PPy (200 nm)	CPCs/iPSCs	Surface properties of conductive polymers controlled Confirmed biocompatibility	2015	[136]
	Electrical conductivity: 0.01–0.37 mS/cm	PCL/gelatin fibers/PPy (216 ± 36 nm and 191 ± 45 nm)	New Zealand white rabbits cardiomyocytes	- Improved attachment and proliferation - Enhanced expression of cardiac--functional protein (α-actinin, Troponin T, and Cx43)	2011	[137]
	By increasing the ratio of PPY in PPY/chitosan hydrogel, the electrical conductivity increased	Chitosan	Rat smooth muscle cells	- <i>In vitro</i> : increased Cx43 expression, faster calcium transfer, and lower calcium transient durations - <i>In vivo</i> : decreasing in the QRS interval, increasing in the transverse activation velocity	2015	[129]
	Electrical conductivity: 0.0072 S/m	PPy nanoparticles (59 ± 6 nm) Gelatin-methacrylate Polyethylene glycol diacrylate PLGA fiber (2.27 μm) with a layer of PPY (320 nm and 0.49 μm)	Neonatal rat ventricular myocyte Human iPSCs	- <i>In vitro</i> : higher Cx43 expression and α-actinin - <i>In vivo</i> : immobilizing cardiomyocytes into scaffolds for a long time, reduce in infarct size	2016	[138]
Polyaniline	Surface resistivity (non-conductive PANI) higher than 10 MΩ/square After partial de-doping, resistivity: 2 kΩ/square Conductivity of pure gelatin 0.005 S/cm By increasing PANI the conductivity increased four fold Electrical current stimulation Electrical stimulation: voltage (10–40 V), frequency 0.5 Hz, 5 ms pulses Not mentioned	PANI	H9c2	Enhanced cell attachment and growth on PANI films	2006	[147]
		Blend: gelatin/PANI (61 ± 13 nm fiber)	H9c2	- Biocompatible - Supporting migration, and proliferation	2006	[148]
		Hyperbranched PLL dendrimers/PANI (69–80 nm)	Rat cardiomyocytes	Higher cell viability and proliferation	2010	[149]
		Polyglycerol dendrimers/PANI (80–180 nm)	Rat cardiomyocytes	- Biocompatible - Supporting cardiomyocytes proliferation - Microcurrent applied to stimulate the differentiation	2011	[150]
	Conductivity of mesh: 3.1 × 10–3 S/cm and electrical stimulation: 1.25 Hz, 5 V/cm	PANI/PLGA fiber (184.7 nm and 101.7 nm)	Neonatal cardiomyocytes	Elongated cardiomyocytes formed isolated cell clusters, beating synchronously, and enhanced expression of Cx43	2013	[130]
	PCL without incorporated PANI shows minimal conductivity (3 × 10–12 S/cm), by increase PANI in the film conductivity increased by up to seven orders of magnitude Electrical stimulation: square wave, frequency of 100 Hz, and electrical potential of 0.5 V	PCL/PANI (50–100 nm)	hMSCs	- Cardiogenic differentiation of hMSCs into cardiomyocytes-like cells - Sarcomeric α-actinin of cardiomyocytes was observed	2011	[142]
		Carboxyl-capped tetraaniline (approx. 265 nm)/(PLA-PEG-PLA) PGS	Fibroblasts, cardiomyocytes, and osteoblasts C2C12	- <i>In vitro</i> : excellent cytocompatibility - <i>In vivo</i> : acceptable biocompatibility, injectable	2013	[151]
	The conductivity close to the native myocardium ranges			Cytocompatibility of the nanocomposites was confirmed	2014	[152]
	Electrical conductivity in 10–5 S/cm	Embedded oligoaniline-polyurethane into PCL films	L929 mouse Fibroblast/HUVECs	Biocompatible - Supporting cell proliferation and attachment - Biodegradable	2014	[153]
	Scaffold's conductivity was 10–5 ± 0.09 S/cm	Aniline pentamer polyurethane/PCL (pore size (several μm to 150 μm))	Neonatal cardiomyocytes	- Cell produced more cardiac specific genes (Actn4 and troponin T-2)	2015	[154]
	Conductivity of this cell delivery vehicles was ~10–3 S/cm	Chitosan-graft-aniline tetramer and dibenzaldehyde-terminated PEG	C2C12 myoblasts and H9c2 cardiac cells	- Biodegradable Biocompatible, injectable and biodegradable self-healing electroactive hydrogels	2016	[155]

PANI increased electrical conductivity, attracted positively charged cell membrane proteins, and improved cell adhesion [130]. Borriello *et al.* used electrospun PANI with biocompatible PCL to make an electrically conductive nanocomposite scaffold. The scaffold promoted hMSC differentiation into cardiomyocyte-like cells [142].

Recently, attempts have been made to incorporate PANI into different hydrogels and polymers in order to yield electrically conductive hydrogels. For example, Cui and his colleagues cultured cardiomyocytes, fibroblasts, and osteoblasts in an injectable hydrogel composed of a polylactide-poly(ethylene glycol)-polylactide (PLA-PEG-PLA) copolymer coated with tetra aniline (with carboxylate modification). Electrical stimulation was applied directly to cells on the tetra aniline-coated samples and enhanced proliferation of all three cell lines was observed [151]. Qazi *et al.* fabricated a conductive cardiac patch by solvent casting PANI doped with camphorsulfonic acid and blended with PGS. The fabricated scaffold demonstrated good biocompatibility and supported attachment, elongation, and proliferation of C2C12 myoblasts. After 4 days, the conductivity of the samples was similar to that of the native myocardium [152].

Baheiraei *et al.* embedded oligoaniline-polyurethane into PCL films to fabricate an electroactive and biocompatible scaffold supporting cell proliferation and attachment. The electrical conductivity of the films was on the order of 10^{-5} S/cm [153]. In another work, Baheiraei *et al.* investigated cardiomyocyte behavior on the PCL films. They observed increased activity of cardiac-specific genes, actinin alpha 4 (Actn4), and troponin T-2 on the conductive substrates, even in the absence of electrical stimulation [154]. Dong *et al.* fabricated antibacterial, self-healing, and electroactive hydrogels by combining chitosan-graft-aniline tetramers with dibenzaldehyde-terminated PEG at physiological conditions. Their results demonstrated that the electroactive hydrogel was biocompatible, injectable, and biodegradable. Additionally, the hydrogel was determined to have an electrical conductivity around 10^{-3} S/cm [155].

5.3. Piezoelectric polymeric materials

Piezoelectric materials generate electric field upon the application of mechanical stress and are able to induce mechanical force in the presence of an electric field [156]. In piezoelectric materials, electric fields are created without an external power source; however, there are limitations on control over the stimulus [27]. There are some studies on piezoelectric scaffolds in nerve [157], skeletal muscle [158], and cardiac tissue engineering. Weber *et al.* investigated *in vitro* cytocompatibility of piezoelectric and electrospun poly(vinylidene fluoride-trifluoroethylene) (PVDF-TrFE) scaffolds [159]. Hitscherich *et al.* developed piezoelectric scaffolds by electrospinning polyvinylidene fluoride (PVDF) and PVDF-TrFE (Fig. 5C.a). Mouse embryonic stem cell-derived cardiomyocytes adhered well to this scaffold and impulsively contracted, exhibited well-organized sarcomeres, and produced cardiac-specific markers including myosin heavy chain, CTT, and Cx43 (Fig. 5C.b and c) [131]. Table 3 provides a summary of scaffolds based on electroactive polymers applied to cardiac tissue engineering.

6. Biocompatibility of electrically conductive nanomaterials

Although electrically conductive nanomaterials offer suitable electrical properties for cardiac tissue engineering, the biocompatibility of these materials varies greatly. While the potential applications of carbon-based nanomaterials continue to expand, their biocompatibility may prevent their use. Several studies have been published showing mixed biological responses to the materials. Lung toxicity to varying extents has been shown for both SWCNTs [54,160] and MWCNTs [53]. These studies found an inflammatory response to the CNTs in addition to granulation around the particles. It is believed that these inflammatory responses are due to long and biopersistent CNTs that are not completely cleared by the immune system [161]. Other studies focusing

on cytotoxicity have shown contrasting evidence. A study on human embryonic kidney cells reported toxicity as SWCNTs inhibited the cell growth by reducing cell adhesion and inducing apoptosis [162]. Cell cycle and biochip analyses showed that the nanotubes down-regulated the production of adhesion proteins (laminin, fibronectin, and collagen IV) and increased expression of apoptosis-associated genes. However, another study by Tamura concluded that the cytotoxic effects were significantly related to the size of CNTs [163]. The study focused on neutrophil response to titanium oxide particles and CNTs in blood and concluded that toxicity is primarily related to the particle size under $3\mu\text{m}$. The reason for the variation in these results likely lies within the broad range of sizes and concentrations of the nanotubes being studied. Therefore, the toxicity of CNTs should be tested in each application prior to integration.

Another study compared the toxicity of CNTs to carbon nanofibers exposed to human lung cancer cell lines [164]. The team conducted an *in vitro* analysis observing the cell proliferation and morphology. They found that the carbon nanofibers were significantly more toxic than the nanotubes. Much of the research on CNT and nanofiber cytotoxicity has been performed on various models of the lung as inhalation is a common method of exposure. Cardiac cells exposed to these nanomaterials in scaffolds may behave differently. Additionally, modulating the size and length of the materials is essential to achieve appropriate biocompatibility. Like other carbon-based nanomaterials, graphene has also been shown to have suitable biocompatibility. A 2012 study by Li *et al.* demonstrated the cytotoxic effects of pristine graphene on macrophages [165]. The murine macrophage-like RAW 264.7 cells were cultured with various concentrations of dissolved and unmodified graphene. A strong dose-dependent biocompatibility for the graphene was observed. Chemically modified graphene has been shown to improve compatibility with cardiac cells. The modification can be obtained using oxidizing [166–168], reducing [169], and functionalizing [170,171] of the graphene sheet.

Unlike carbon-based nanomaterials, materials using gold have shown remarkable compatibility in many studies. For example, Shukla *et al.* showed that gold nanoparticles did not have any adverse biological impact and are biocompatible when studied with macrophages [172]. The cytotoxicity of the nanoparticles on RAW 264.7 macrophages was studied with MTT assay and the macrophages maintained viability after 72 h. Additionally, Goodman and colleagues demonstrated the cytocompatibility of gold nanoparticles with tethered ionic side chains [173]. They found that cationic modifications increased cytotoxicity while anionic molecules showed little to no negative effects on cell biocompatibility of the nanomaterials.

The biocompatibility of electroactive polymers varies significantly depending on specific polymer(s) used. Polymers such as PPy have been shown to be biocompatible with limited inflammatory response after implantation *in vivo* [132]. PPy was tested *in vivo* and *in vitro* on rat peripheral nerve tissue and was observed to be biocompatible. PANI has also been studied and has shown great biocompatibility with H9c2 cardiac myoblasts [147]. While an initial reduction in the cell growth and adhesion was observed, morphologically identical monolayers were formed on the PANI-coated surfaces compared to polystyrene surfaces after 6 days. Additionally, the polymer maintained conductivity for 100 h after coating. Another study on polylactide-aniline pentamer (PLAAP) copolymers also demonstrated excellent cytocompatibility with rat glioma cells [143]. Cell viability (measured with MTT assay) was the highest for cells cultured on PLAAP compared to PLA and aniline pentamer (AP) individually. The last electroactive polymer discussed in this review was PVDF-TrFE; a study found that human skin fibroblasts proliferated normally on PVDF-TrFE in comparison to those cultured on conventional polystyrene dish [159].

For these materials to be used in cardiac tissue engineering, it is imperative that they have required physical, electrical, and biological properties. For some materials, such as graphene, simple modifications can be made to tailor their surface for specific biomedical application.

However, other materials may have inherent limitations that impair their utility as conductive materials for tissue engineering.

7. Concluding remarks and future challenges

Cardiovascular diseases, involving the heart and/or blood vessels, are a primary cause of death in the 21st century. Cardiac tissue engineering has the potential to introduce suitable materials and procedures to serve as innovative alternative treatment strategies to heart transplantation. Despite the considerable achievements in recent years, scientists have faced many limitations in creating functional, engineered myocardial tissues at clinical levels [174]. Promoting the electrical integration of an engineered tissue with the host myocardium can help restore functionality in a failing heart. Regulated beating of the heart is highly dependent on the structure and chemistry of the ECM. Engineered cardiac scaffolds require mimicked anisotropic structure of the native myocardial ECM, electrical conductivity of the cardiac tissue (0.16 S/m longitudinally and 0.005 S/m transversely), and recreation of the unique mechanical properties of the myocardium (highly aligned collagen nanofibers 10–100 nm) that can be obtained by tuning the scaffold's biochemical, biophysical, and topographical features. There have also been attempts to apply frequent and regular electrical stimulation to engineered tissues, resulting more functional cardiac constructs.

Tissue engineering scaffolds containing electrically conductive nanostructured materials are able to mimic the myocardial ECM [175]. Moreover, they have been proven to support electromechanical integration of cardiomyocytes within the host myocardium after transplantation. There are a wide range of conductive nanostructured materials for cardiac tissue engineering. These include carbon-based nanomaterials (CNTs, CNFs, and graphene), gold-based nanomaterials, and electroactive polymers (such as PANI, PPy, and piezoelectric polymeric materials). Apart from developments in the chemistry of scaffolds, the fabrication techniques are also moving forward from conventional methods to innovative 3D manufacturing. Scientists from multiple disciplines have worked together to facilitate cardiomyocyte communication through a myriad of strategies including electrically conductive scaffolds and gene transfer techniques. The ultimate goal in cardiac tissue engineering is to induce the creation of specific cardiac gap junction proteins to enable the production of functional tissue constructs. Substantial interest in the scientific community has revolved around the use of electroactive nanostructured materials due to their great potential in cardiac tissue engineering. In addition, state-of-the-art fabrication techniques will assist electrically conductive scaffolds for improved functionality. Although nanostructured gold particles, carbon-based materials, and electroactive polymers have shed light on the preparation of promising scaffolds and patches, there are still unexplored biomaterials and fabrication strategies with potential to revolutionize the field. There are still many unanswered questions regarding different aspects of these biomaterials, such as their biocompatibility, biodegradability, injectability, and aptitude for surface functionalization. Moreover, it is important to better explore the effects of these biomaterials on differentiation of cardiomyogenic stem cells, their adherence, elongation, orientation, and functional properties as these properties relate to the development of functional cardiac tissues. Undoubtedly, more investigation on the use of electrically conductive nanostructured materials in cardiac tissue engineering must be pursued to answer the critical questions in the field. Due to the interdisciplinary nature of the field, materials scientists, biologists, engineers, and physicians should work together to develop new technology in the pursuit of surmounting the challenges of cardiac tissue engineering.

Acknowledgements

The authors have no competing interests. The authors also would like to acknowledge funding from the National Institutes of Health

(EB021857, GM126571), and American Heart Association Transformational Project Award (18TPA34230036).

References

- [1] V.L. Roger, A.S. Go, D.M. Lloyd-Jones, E.J. Benjamin, J.D. Berry, W.B. Borden, D.M. Bravata, S. Dai, E.S. Ford, C.S. Fox, H.J. Fullerton, C. Gillespie, S.M. Hailpern, J.A. Heit, V.J. Howard, B.M. Kissela, S.J. Kittner, D.T. Lackland, J.H. Lichtman, L.D. Lisabeth, D.M. Makuc, G.M. Marcus, A. Marelli, D.B. Matchar, C.S. Moy, D. Mozaffarian, M.E. Mussolino, G. Nichol, N.P. Paynter, E.Z. Soliman, P.D. Sorlie, N. Sotoodehnia, T.N. Turan, S.S. Virani, N.D. Wong, D. Woo, M.B. Turner, Heart disease and stroke statistics – 2012 update: a report from the American Heart Association, *Circulation* 125 (1) (2012) <https://doi.org/10.1161/CIR.0b013e31823ac046>.
- [2] M. Chiong, Z.V. Wang, Z. Pedrozo, D.J. Cao, R. Troncoso, M. Ibáñez, A. Criollo, A. Nemchenko, J.A. Hill, S. Lavandero, Cardiomyocyte death: mechanisms and translational implications, *Cell Death Dis.* 2 (12) (2011) <https://doi.org/10.1038/cddis.2011.130>.
- [3] W.E. Cascio, T.A. Johnson, L.S. Gettes, Electrophysiologic changes in ischemic ventricular myocardium: I. Influence of ionic, metabolic, and energetic changes, *J. Cardiovasc. Electrophysiol.* 6 (11) (1995) 1039–1062.
- [4] G. Vunjak-Novakovic, K.O. Lui, N. Tandon, K.R. Chien, Bioengineering heart muscle: a paradigm for regenerative medicine, *Annu. Rev. Biomed. Eng.* 13 (2011) 245–267 <https://doi.org/10.1146/annurev-bioeng-071910-124701>.
- [5] M.A. Laflamme, C.E. Murry, Heart regeneration, *Nature* 473 (7347) (2011) 326–335 <https://doi.org/10.1038/nature10147>.
- [6] K.A. Jackson, S.M. Majka, H. Wang, J. Pocius, C.J. Hartley, M.W. Majesky, M.L. Entman, L.H. Michael, K.K. Hirschi, M.A. Goodell, Regeneration of ischemic cardiac muscle and vascular endothelium by adult stem cells, *J. Clin. Invest.* 107 (11) (2001) 1395–1402 <https://doi.org/10.1172/jci12150>.
- [7] C. Toma, M.F. Pittenger, K.S. Cahill, B.J. Byrne, P.D. Kessler, Human mesenchymal stem cells differentiate to a cardiomyocyte phenotype in the adult murine heart, *Circulation* 105 (1) (2002) 93–98.
- [8] I. Kehat, D. Kenyagin-Karsenti, M. Snir, H. Segev, M. Amit, A. Gepstein, E. Livne, O. Binah, J. Itskovitz-Eldor, L. Gepstein, Human embryonic stem cells can differentiate into myocytes with structural and functional properties of cardiomyocytes, *J. Clin. Invest.* 108 (3) (2001) 407–414 <https://doi.org/10.1172/jci12131>.
- [9] C.L. Mummery, J. Zhang, E.S. Ng, D.A. Elliott, A.G. Elefanty, T.J. Kamp, Differentiation of human embryonic stem cells and induced pluripotent stem cells to cardiomyocytes: a methods overview, *Circ. Res.* 111 (3) (2012) 344–358 <https://doi.org/10.1161/circresaha.110.227512>.
- [10] S. Dimmeler, J. Burchfield, A.M. Zeiher, Cell-based therapy of myocardial infarction, *Arterioscler. Thromb. Vasc. Biol.* 28 (2) (2008) 208–216 <https://doi.org/10.1161/atvbaha.107.155317>.
- [11] W.H. Zimmermann, T. Eschenhagen, Cardiac tissue engineering for replacement therapy, *Heart Fail. Rev.* 8 (3) (2003) 259–269.
- [12] T. Dvir, B.P. Timko, D.S. Kohane, R. Langer, Nanotechnological strategies for engineering complex tissues, *Nat. Nanotechnol.* 6 (1) (2011) 13–22 <https://doi.org/10.1038/nnano.2010.246>.
- [13] Z. Li, J. Guan, Hydrogels for cardiac tissue engineering, *Polymers* 3 (2) (2011) <https://doi.org/10.3390/polym3020740>.
- [14] R. Langer, J.P. Vacanti, Tissue engineering, *Science* 260 (5110) (1993) 920–926.
- [15] L. Ye, W.H. Zimmermann, D.J. Garry, J. Zhang, Patching the heart: cardiac repair from within and outside, *Circ. Res.* 113 (7) (2013) 922–932 <https://doi.org/10.1161/circresaha.113.300216>.
- [16] A. Hasan, A. Khattab, M.A. Islam, K.A. Hweij, J. Zeitouny, R. Waters, M. Sayegh, M.M. Hossain, A. Paul, Injectable hydrogels for cardiac tissue repair after myocardial infarction, *Adv. Sci.* 2 (11) (2015) <https://doi.org/10.1002/adv.201500122>.
- [17] W.J. Li, C.T. Laurencin, E.J. Caterson, R.S. Tuan, F.K. Ko, Electrospun nanofibrous structure: a novel scaffold for tissue engineering, *J. Biomed. Mater. Res.* 60 (4) (2002) 613–621.
- [18] X. Zong, H. Bien, C.Y. Chung, L. Yin, D. Fang, B.S. Hsiao, B. Chu, E. Entcheva, Electrospun fine-textured scaffolds for heart tissue constructs, *Biomaterials* 26 (26) (2005) 5330–5338 <https://doi.org/10.1016/j.biomaterials.2005.01.052>.
- [19] H.T. Au, I. Cheng, M.F. Chowdhury, M. Radisic, Interactive effects of surface topography and pulsatile electrical field stimulation on orientation and elongation of fibroblasts and cardiomyocytes, *Biomaterials* 28 (29) (2007) 4277–4293 <https://doi.org/10.1016/j.biomaterials.2007.06.001>.
- [20] I. Armentano, M. Dottori, E. Fortunati, S. Mattioli, J.M. Kenny (Eds.), Biodegradable polymer matrix nanocomposites for tissue engineering: a review, *Polym. Degrad. Stab.* 95 (2010) 2126–2146.
- [21] B.S. Harrison, A. Atala, Carbon nanotube applications for tissue engineering, *Biomaterials* 28 (2) (2007) 344–353 <https://doi.org/10.1016/j.biomaterials.2006.07.044>.
- [22] G. Vunjak-Novakovic, N. Tandon, A. Godier, R. Muidhof, A. Marsano, T.P. Martens, M. Radisic, Challenges in cardiac tissue engineering, *Tissue Eng. B Rev.* 16 (2) (2010) 169–187 <https://doi.org/10.1089/ten.TEB.2009.0352>.
- [23] R. Muidhof, N. Tandon, E.J. Lee, J. Luo, Y. Duan, K. Yeager, E. Konofagou, G. Vunjak-Novakovic, Biomimetic perfusion and electrical stimulation applied in concert improved the assembly of engineered cardiac tissue, *J. Tissue Eng. Regen. Med.* 6 (10) (2012) <https://doi.org/10.1002/term.525>.
- [24] J. Guan, F. Wang, Z. Li, J. Chen, X. Guo, J. Liao, N.I. Moldovan, The stimulation of the cardiac differentiation of mesenchymal stem cells in tissue constructs that mimic myocardium structure and biomechanics, *Biomaterials* 32 (24) (2011) 5568–5580 <https://doi.org/10.1016/j.biomaterials.2011.04.038>.

- [25] S. Ahadian, A. Khademhosseini, Smart scaffolds in tissue regeneration, *Regen. Biomater.* 5 (3) (2018) 125–128.
- [26] M. Montgomery, S. Ahadian, L.D. Huyer, M.L. Rito, R.A. Civitarese, R.D. Vanderlaan, J. Wu, L.A. Reis, A. Momen, S. Akbari, Flexible shape-memory scaffold for minimally invasive delivery of functional tissues, *Nat. Mater.* 16 (10) (2017) 1038.
- [27] R. Balint, N.J. Cassidy, S.H. Cartmell, Conductive polymers: towards a smart biomaterial for tissue engineering, *Acta Biomater.* 10 (6) (2014) 2341–2353.
- [28] N. Narita, M. Bielinska, D.B. Wilson, Cardiomyocyte differentiation by GATA-4-deficient embryonic stem cells, *Development* 124 (1997) 3755–3764.
- [29] M.J. Doyle, J.L. Lohr, C.S. Chapman, N. Koyano-Nakagawa, M.G. Garry, D.J. Garry, Human induced pluripotent stem cell-derived cardiomyocytes as a model for heart development and congenital heart disease, *Stem Cell Rev. Rep.* 11 (5) (2015) 710–727.
- [30] X. Yu, J. Zou, Z. Ye, H. Hammond, G. Chen, A. Tokunaga, P. Mali, Y.-M. Li, C. Civin, N. Gaiano, Notch signaling activation in human embryonic stem cells is required for embryonic, but not trophoblastic, lineage commitment, *Cell Stem Cell* 2 (5) (2008) 461–471.
- [31] J.-Q. He, Y. Ma, Y. Lee, J.A. Thomson, T.J. Kamp, Human embryonic stem cells develop into multiple types of cardiac myocytes: action potential characterization, *Circ. Res.* 93 (1) (2003) 32–39.
- [32] V. Tanwar, J.B. Bylund, J. Hu, J. Yan, J.M. Walthall, A. Mukherjee, W.H. Heaton, W.D. Wang, F. Potet, M. Rai, Gremlin 2 promotes differentiation of embryonic stem cells to atrial fate by activation of the JNK signaling pathway, *Stem Cells* 32 (7) (2014) 1774–1788.
- [33] G. Lu, H.K. Haider, S. Jiang, M. Ashraf, Sca-1+ stem cell survival and engraftment in the infarcted heart: dual role for preconditioning induced connexin-43, *Circulation* 119 (19) (2009) 2587.
- [34] M.A. Retamal, K.A. Schalper, K.F. Shoji, J.A. Orellana, M.V.L. Bennett, J.C. Sáez, Possible involvement of different connexin43 domains in plasma membrane permeabilization induced by ischemia-reperfusion, *J. Membr. Biol.* 218 (1–3) (2007) 49–63.
- [35] W. Roell, T. Lewalter, P. Sasse, Y.N. Tallini, B.-R. Choi, M. Breitbach, R. Doran, U.M. Becher, S.-M. Hwang, T. Bostani, Engraftment of connexin 43-expressing cells prevents post-infarct arrhythmia, *Nature* 450 (7171) (2007) 819.
- [36] R. Chaudhuri, M. Ramachandran, P. Moharil, M. Harumalani, A.K. Jaiswal, *Biomaterials and cells for cardiac tissue engineering: current choices*, *Mater. Sci. Eng. C* 79 (2017) 950–957.
- [37] H. Savoji, M.H. Mohammadi, N. Rafatian, M.K. Toroghi, E.Y. Wang, Y. Zhao, A. Korolj, S. Ahadian, M. Radisic, Cardiovascular disease models: a game changing paradigm in drug discovery and screening, *Biomaterials* 198 (2019) 3–26.
- [38] Q.-Z. Chen, S.E. Harding, N.N. Ali, A.R. Lyon, A.R. Boccacini, *Biomaterials in cardiac tissue engineering: ten years of research survey*, *Mater. Sci. Eng. R. Rep.* 59 (1–6) (2008) 1–37.
- [39] M.T. Alrfai, D. Murali, A. Paul, K.M. Ridwan, J.M. Connell, D. Shum-Tim, Cardiac tissue engineering and regeneration using cell-based therapy, *Stem Cells Cloning* 8 (2015) 81.
- [40] D.A. Taylor, L.C. Sampaio, A. Gobin, Building new hearts: a review of trends in cardiac tissue engineering, *Am. J. Transplant.* 14 (11) (2014) 2448–2459.
- [41] S. Ahadian, R. Obregón, J. Ramón-Azcón, G. Salazar, H. Shiku, M. Ramalingam, T. Matsue, Carbon nanotubes and graphene-based nanomaterials for stem cell differentiation and tissue regeneration, *J. Nanosci. Nanotechnol.* 16 (9) (2016) 8862–8880.
- [42] S. Ahadian, S. Yamada, M. Estili, X. Liang, R.B. Sadeghian, K. Nakajima, H. Shiku, T. Matsue, A. Khademhosseini, Carbon nanotubes embedded in embryoid bodies direct cardiac differentiation, *Biomed. Microdevices* 19 (3) (2017) 57.
- [43] J. Ramón-Azcón, S. Ahadian, R. Obregón, H. Shiku, M. Ramalingam, T. Matsue, Applications of carbon nanotubes in stem cell research, *J. Biomed. Nanotechnol.* 10 (10) (2014) 2539–2561.
- [44] T. Fujie, S. Ahadian, H. Liu, H. Chang, S. Ostrovidov, H. Wu, H. Bae, K. Nakajima, H. Kaji, A. Khademhosseini, Engineered nanomembranes for directing cellular organization toward flexible biodevices, *Nano Lett.* 13 (7) (2013) 3185–3192.
- [45] J. Ramón-Azcón, S. Ahadian, M. Estili, X. Liang, S. Ostrovidov, H. Kaji, H. Shiku, M. Ramalingam, K. Nakajima, Y. Sakka, Dielectrophoretically aligned carbon nanotubes to control electrical and mechanical properties of hydrogels to fabricate contractile muscle myofibers, *Adv. Mater.* 25 (29) (2013) 4028–4034.
- [46] J.-P. Salvétat, J.-M. Bonard, N.H. Thomson, A.J. Kulik, L. Forró, W. Benoit, L. Zuppiroli, Mechanical properties of carbon nanotubes, *Appl. Phys. A* 69 (3) (1999) 255–260, <https://doi.org/10.1007/s003390050999>.
- [47] C. Journet, W.K. Maser, P. Bernier, A. Loiseau, M.L. de La Chapelle, S. Lefrant, P. Deniard, R. Lee, J.E. Fischer, Large-scale production of single-walled carbon nanotubes by the electric-arc technique, *Nature* 388 (1997) 756–758, <https://doi.org/10.1038/41972>.
- [48] A. Thess, R. Lee, P. Nikolaev, H. Dai, P. Petit, J. Robert, C. Xu, Y.H. Lee, S.G. Kim, A.G. Rinzler, D.T. Colbert, G.E. Scuseria, D. Tománek, J.E. Fischer, R.E. Smalley, Crystalline ropes of metallic carbon nanotubes, *Science* 273 (7) (1996) 483, <https://doi.org/10.1126/science.273.5274.483>.
- [49] A.M. Cassell, J.A. Raymakers, J. Kong, H. Dai, Large scale CVD synthesis of single-walled carbon nanotubes, *J. Phys. Chem. B* 103 (31) (1999) 6484–6492, <https://doi.org/10.1021/jp990957s>.
- [50] A. Abarrategi, M.C. Gutierrez, C. Moreno-Vicente, M.J. Hortiguera, F. Ramos, J.L. Lopez-Lacomba, M.L. Ferrer, F. del Monte, Multiwall carbon nanotube scaffolds for tissue engineering purposes, *Biomaterials* 29 (1) (2008) 94–102, <https://doi.org/10.1016/j.biomaterials.2007.09.021>.
- [51] M.A. Correa-Duarte, N. Wagner, J. Rojas-Chapana, C. Morsczech, M. Thie, M. Giersig, Fabrication and biocompatibility of carbon nanotube-based 3D networks as scaffolds for cell seeding and growth, *Nano Lett.* 4 (11) (2004) 2233–2236, <https://doi.org/10.1021/nl048574f>.
- [52] G. Jia, H. Wang, L. Yan, X. Wang, R. Pei, T. Yan, Y. Zhao, X. Guo, Cytotoxicity of carbon nanomaterials: single-wall nanotube, multi-wall nanotube, and fullerene, *Environ. Sci. Technol.* 39 (5) (2005) 1378–1383.
- [53] J. Muller, F. Huan, N. Moreau, P. Misson, J.-F. Heilier, M. Delos, M. Arras, A. Fonseca, J.B. Nagy, D. Lison, Respiratory toxicity of multi-wall carbon nanotubes, *Toxicol. Appl. Pharmacol.* 207 (3) (2005) 221–231.
- [54] D.B. Warheit, B.R. Laurence, K.L. Reed, D.H. Roach, G.A.M. Reynolds, T.R. Webb, Comparative pulmonary toxicity assessment of single-wall carbon nanotubes in rats, *Toxicol. Sci.* 77 (1) (2004) 117–125, <https://doi.org/10.1093/toxsci/kfg228>.
- [55] J.V. Veetil, K. Ye, Tailored carbon nanotubes for tissue engineering applications, *Biotechnol. Prog.* 25 (3) (2009) 709–721, <https://doi.org/10.1002/bt.165>.
- [56] S.K. Smart, A.I. Cassady, G.Q. Lu, D.J. Martin, The biocompatibility of carbon nanotubes, *Carbon* 44 (6) (2006) 1034–1047.
- [57] S.R. Shin, S.M. Jung, M. Zalabany, K. Kim, P. Zorlutuna, S.B. Kim, M. Nikkhah, M. Khabiry, M. Azize, J. Kong, K.T. Wan, T. Palacios, M.R. Dokmeci, H. Bae, X.S. Tang, A. Khademhosseini, Carbon-nanotube-embedded hydrogel sheets for engineering cardiac constructs and bioactuators, *ACS Nano* 7 (3) (2013) 2369–2380.
- [58] A.M. Martins, G. Eng, S.G. Caridade, J.F. Mano, R.L. Reis, G. Vunjak-Novakovic, Electrically conductive chitosan/carbon scaffolds for cardiac tissue engineering, *Biomacromolecules* 15 (2) (2014) 635–643, <https://doi.org/10.1021/bm401679q>.
- [59] E. Mooney, J.N. Mackle, D.J. Blond, E. O'Carbhaill, G. Shaw, W.J. Blau, F.P. Barry, V. Barron, J.M. Murphy, The electrical stimulation of carbon nanotubes to provide a cardiomyogenic cue to MSCs, *Biomaterials* 33 (26) (2012) 6132–6139, <https://doi.org/10.1016/j.biomaterials.2012.05.032>.
- [60] D.Y. Lewitus, J. Landers, J. Branch, K.L. Smith, G. Callegari, J. Kohn, A.V. Neimark, Biohybrid carbon nanotube/agarose fibers for neural tissue engineering, *Adv. Funct. Mater.* 21 (14) (2011) 2624–2632, <https://doi.org/10.1002/adfm.201002429>.
- [61] M.A. Shokrgozar, F. Mottaghiab, V. Mottaghiab, M. Farokhi, Fabrication of porous chitosan/poly(vinyl alcohol) reinforced single-walled carbon nanotube nanocomposites for neural tissue engineering, *J. Biomed. Nanotechnol.* 7 (2) (2011) 276–284.
- [62] W. Yang, P. Thordarson, J.J. Gooding, S.P. Ringer, F. Braet, Carbon nanotubes for biological and biomedical applications, *Nanotechnology* 18 (41) (2007), 412001, <https://doi.org/10.1088/0957-4484/18/41/412001>.
- [63] S. Garibaldi, C. Brunelli, V. Bavastrello, G. Ghigliotti, C. Nicolini, Carbon nanotube biocompatibility with cardiac muscle cells, *Nanotechnology* 17 (2) (2005) 391–397, <https://doi.org/10.1088/0957-4484/17/2/008>.
- [64] V. Martinelli, G. Cellot, F.M. Toma, C.S. Long, J.H. Caldwell, L. Zentilin, M. Giacca, A. Turco, M. Prato, L. Ballerini, L. Mestroni, Carbon nanotubes promote growth and spontaneous electrical activity in cultured cardiac myocytes, *Nano Lett.* 12 (4) (2012) 1831–1838, <https://doi.org/10.1021/nl204064s>.
- [65] V. Martinelli, G. Cellot, F.M. Toma, C.S. Long, J.H. Caldwell, L. Zentilin, M. Giacca, A. Turco, M. Prato, L. Ballerini, L. Mestroni, Carbon nanotubes instruct physiological growth and functionally mature syncytia: nongenetic engineering of cardiac myocytes, *ACS Nano* 7 (7) (2013) 5746–5756, <https://doi.org/10.1021/nn4002193>.
- [66] H. Liao, R. Qi, M. Shen, X. Cao, R. Guo, Y. Zhang, X. Shi, Improved cellular response on multiwalled carbon nanotube-incorporated electrosurf polyvinyl alcohol/chitosan nanofibrous scaffolds, *Colloids Surf. B Biointerfaces* 84 (2) (2011) 528–535, <https://doi.org/10.1016/j.colsurfb.2011.02.010>.
- [67] A.M. Wickham, M.M. Islam, D. Mondal, J. Phopase, V. Sadhu, E. Tamas, N. Poliseti, A. Richter-Dahlfors, B. Liedberg, M. Griffith, Polycaprolactone-thiophene-conjugated carbon nanotube meshes as scaffolds for cardiac progenitor cells, *J. Biomed. Mater. Res. B Appl. Biomater.* 102 (7) (2014) 1553–1561, <https://doi.org/10.1002/jbm.b.33136>.
- [68] M. Kharazizha, S.R. Shin, M. Nikkhah, S.N. Topkaya, N. Masoumi, N. Annabi, M.R. Dokmeci, A. Khademhosseini, Tough and flexible CNT-polymeric hybrid scaffolds for engineering cardiac constructs, *Biomaterials* 35 (26) (2014) 7346–7354, <https://doi.org/10.1016/j.biomaterials.2014.05.014>.
- [69] S. Pok, F. Vitale, S.L. Eichmann, O.M. Benavides, M. Pasquali, J.G. Jacot, Biocompatible carbon nanotube-chitosan scaffold matching the electrical conductivity of the heart, *ACS Nano* 8 (10) (2014) 9822–9832, <https://doi.org/10.1021/nn503693h>.
- [70] S.W. Crowder, Y. Liang, R. Rath, A.M. Park, S. Maltas, P.N. Pintaura, W. Hofmeister, C.C. Lim, X. Wang, H.J. Sung, Poly(epsilon-caprolactone)-carbon nanotube composite scaffolds for enhanced cardiac differentiation of human mesenchymal stem cells, *Nanomedicine (Lond.)* 8 (11) (2013) 1763–1776, <https://doi.org/10.2217/nmm.12.204>.
- [71] J. Park, R.S. Lakes, *Biomaterials: An Introduction*, 3rd ed. Springer-Verlag, New York, 2007, 562.
- [72] H. Elkenany, L. Amelse, A. Lafont, S. Bourdo, M. Caldwell, N. Neilsen, E. Dervishi, O. Derek, A.S. Biris, D. Anderson, M. Dhar, Graphene supports in vitro proliferation and osteogenic differentiation of goat adult mesenchymal stem cells: potential for bone tissue engineering, *J. Appl. Toxicol.* 35 (4) (2015) 367–374, <https://doi.org/10.1002/jat.3024>.
- [73] H. Yu, H. Zhao, C. Huang, Y. Du, Mechanically and electrically enhanced CNT-collagen hydrogels as potential scaffolds for engineered cardiac constructs, *ACS Biomater. Sci. Eng.* 3 (11) (2017) 3017–3021, <https://doi.org/10.1021/acsbomaterials.6b00620>.
- [74] S. Ahadian, L. Davenport Huyer, M. Estili, B. Yee, N. Smith, Z. Xu, Y. Sun, M. Radisic, Moldable elastomeric polyester-carbon nanotube scaffolds for cardiac tissue engineering, *Acta Biomater.* 52 (2017) 81–91, <https://doi.org/10.1016/j.actbio.2016.12.009>.

- [75] C.M. Ho, A. Mishra, P.T. Lin, S.H. Ng, W.Y. Yeong, Y.J. Kim, Y.J. Yoon, 3D printed polycaprolactone carbon nanotube composite scaffolds for cardiac tissue engineering, *Macromol. Biosci.* 17 (4) (2017) <https://doi.org/10.1002/mabi.201600250>.
- [76] M. Izadifar, D. Chapman, P. Babyn, X. Chen, M.E. Kelly, UV-assisted 3D bioprinting of nanoreinforced hybrid cardiac patch for myocardial tissue engineering, *Tissue Eng. Part C, Methods* 24 (2) (2018) 74–88 <https://doi.org/10.1089/ten.TEC.2017.0346>.
- [77] K. Roshanbifar, J. Hilborn, O.P. Varghese, O.P. Oommen, Injectable and thermoresponsive pericardial matrix derived conductive scaffold for cardiac tissue engineering, *RSC Adv.* 7 (51) (2017) 31980–31988, <https://doi.org/10.1039/C7RA03780E>.
- [78] M. Cabiati, F. Vozzi, F. Gemma, F. Montemurro, C. De Maria, G. Vozzi, C. Domenici, S. Del Ry, Cardiac tissue regeneration: a preliminary study on carbon-based nanotubes gelatin scaffold, *J. Biomed. Mater. Res. B Appl. Biomater.* 106 (8) (2018) 2750–2762 <https://doi.org/10.1002/jbm.b.34056>.
- [79] B. Maruyama, K. Alam, Carbon nanotubes and nanofibers in composite materials, *SAMPE J.* 38 (3) (2002) 59–70.
- [80] S. Bal, Experimental study of mechanical and electrical properties of carbon nanofiber/epoxy composites, *Mater. Des.* (1980–2015) 31 (5) (2010) 2406–2413.
- [81] K.L. Klein, A.V. Melechko, T.E. McKnight, S.T. Retterer, P.D. Rack, J.D. Fowlkes, D.C. Joy, M.L. Simpson, Surface characterization and functionalization of carbon nanofibers, *J. Appl. Phys.* 103 (6) (2008) 3.
- [82] N. Rodriguez, A review of catalytically grown carbon nanofibers, *J. Mater. Res.* 8 (12) (1993) 3233–3250.
- [83] L. Feng, N. Xie, J. Zhong, Carbon nanofibers and their composites: a review of synthesizing, properties and applications, *Materials* 7 (5) (2014) 3919–3945.
- [84] E. Mirzaei, J. Ai, S. Ebrahimi-Barough, J. Verdi, H. Ghanbari, R. Faridi-Majidi, The differentiation of human endometrial stem cells into neuron-like cells on electrospon PAN-derived carbon nanofibers with random and aligned topographies, *Mol. Neurobiol.* 53 (7) (2016) 4798–4808.
- [85] T.B. Nguyen-Vu, H. Chen, A.M. Cassell, R. Andrews, M. Meyyappan, J. Li, Vertically aligned carbon nanofiber arrays: an advance toward electrical–neural interfaces, *Small* 2 (1) (2006) 89–94.
- [86] R.L. Price, M.C. Waid, K.M. Habershtro, T.J. Webster, Selective bone cell adhesion on formulations containing carbon nanofibers, *Biomaterials* 24 (11) (2003) 1877–1887.
- [87] R.L. Price, K. Ellison, K.M. Habershtro, T.J. Webster, Nanometer surface roughness increases select osteoblast adhesion on carbon nanofiber compacts, *J. Biomed. Mater. Res. A* 70 (1) (2004) 129–138.
- [88] D. Khang, M. Sato, R.L. Price, A.E. Ribbe, T.J. Webster, Selective adhesion and mineral deposition by osteoblasts on carbon nanofiber patterns, *Int. J. Nanomedicine* 1 (1) (2006) 65.
- [89] C. Zhang, D. Cheng, T. Tang, X. Jia, Q. Cai, X. Yang, Nanoporous structured carbon nanofiber–bioactive glass composites for skeletal tissue regeneration, *J. Mater. Chem. B* 3 (26) (2015) 5300–5309.
- [90] S. Ahadian, J. Ramón-Azcón, M. Estili, X. Liang, S. Ostrovidov, H. Shiku, M. Ramalingam, K. Nakajima, Y. Sakka, H. Bae, Hybrid hydrogels containing vertically aligned carbon nanotubes with anisotropic electrical conductivity for muscle myofiber fabrication, *Sci. Rep.* 4 (2014) 4271.
- [91] D.A. Stout, B. Basu, T.J. Webster, Poly (lactic–co–glycolic acid): carbon nanofiber composites for myocardial tissue engineering applications, *Acta Biomater.* 7 (8) (2011) 3101–3112.
- [92] X. Meng, D.A. Stout, L. Sun, R.L. Beingessner, H. Fenniri, T.J. Webster, Novel injectable biomimetic hydrogels with carbon nanofibers and self assembled rosette nanotubes for myocardial applications, *J. Biomed. Mater. Res. A* 101 (4) (2013) 1095–1102.
- [93] A.M. Asiri, H.M. Marwani, S.B. Khan, T.J. Webster, Greater cardiomyocyte density on aligned compared with random carbon nanofibers in polymer composites, *Int. J. Nanomedicine* 9 (2014) 5533.
- [94] S. Ahadian, U. Naito, V.J. Surya, S. Darvishi, M. Estili, X. Liang, K. Nakajima, H. Shiku, Y. Kawazoe, T. Matsue, Fabrication of poly (ethylene glycol) hydrogels containing vertically and horizontally aligned graphene using dielectrophoresis: an experimental and modeling study, *Carbon* 123 (2017) 460–470.
- [95] S.R. Shin, Y.-C. Li, H.L. Jang, P. Khoshakhlagh, M. Akbari, A. Nasajpour, Y.S. Zhang, A. Tamayol, A. Khademhosseini, Graphene-based materials for tissue engineering, *Adv. Drug Deliv. Rev.* 105 (2016) 255–274.
- [96] S. Ahadian, Y. Zhou, S. Yamada, M. Estili, X. Liang, K. Nakajima, H. Shiku, T. Matsue, Graphene induces spontaneous cardiac differentiation in embryoid bodies, *Nano-scale* 8 (13) (2016) 7075–7084.
- [97] S. Darvishi, M. Souissi, F. Karimzadeh, M. Kharaziha, R. Sahara, S. Ahadian, Ni nanoparticle-decorated reduced graphene oxide for non-enzymatic glucose sensing: an experimental and modeling study, *Electrochim. Acta* 240 (2017) 388–398.
- [98] K. Yang, L. Feng, X. Shi, Z. Liu, Nano-graphene in biomedicine: theranostic applications, *Chem. Soc. Rev.* 42 (2) (2013) 530–547.
- [99] J. Wang, C. Cui, H. Nan, Y. Yu, Y. Xiao, E. Poon, G. Yang, X. Wang, C. Wang, L. Li, Graphene sheet-induced global maturation of cardiomyocytes derived from human induced pluripotent stem cells, *ACS Appl. Mater. Interfaces* 9 (31) (2017) 25929–25940.
- [100] A.S. Smith, H. Yoo, H. Yi, E.H. Ahn, J.H. Lee, G. Shao, E. Nagornyak, M.A. Laflamme, C.E. Murry, D.-H. Kim, Micro- and nano-patterned conductive graphene–PEG hybrid scaffolds for cardiac tissue engineering, *Chem. Commun.* 53 (53) (2017) 7412–7415.
- [101] L.J. Cote, J. Kim, V.C. Tung, J. Luo, F. Kim, J. Huang, Graphene oxide as surfactant sheets, *Pure Appl. Chem.* 83 (1) (2010) 95–110.
- [102] A. Bagri, C. Mattevi, M. Acik, Y.J. Chabal, M. Chhowalla, V.B. Shenoy, Structural evolution during the reduction of chemically derived graphene oxide, *Nat. Chem.* 2 (7) (2010) 581.
- [103] S.R. Shin, B. Aghaei-Ghareh-Bolagh, T.T. Dang, S.N. Topkaya, X. Gao, S.Y. Yang, S.M. Jung, J.H. Oh, M.R. Dokmeci, X. Tang, Cell-laden microengineered and mechanically tunable hybrid hydrogels of gelatin and graphene oxide, *Adv. Mater.* 25 (44) (2013) 6385–6391.
- [104] S.R. Shin, B. Aghaei-Ghareh-Bolagh, X. Gao, M. Nikkhah, S.M. Jung, A. Dolatshahi-Pirouz, S.B. Kim, S.M. Kim, M.R. Dokmeci, X. Tang, Layer-by-layer assembly of 3D tissue constructs with functionalized graphene, *Adv. Funct. Mater.* 24 (39) (2014) 6136–6144.
- [105] S.R. Shin, C. Zihlmann, M. Akbari, P. Assawes, L. Cheung, K. Zhang, V. Manoharan, Y.S. Zhang, M. Yüsekaya, Kt Wan, Reduced graphene oxide–gelMA hybrid hydrogels as scaffolds for cardiac tissue engineering, *Small* 12 (27) (2016) 3677–3689.
- [106] S.R. Shin, C. Shin, A. Memic, S. Shadmehr, M. Miscuglio, H.Y. Jung, S.M. Jung, H. Bae, A. Khademhosseini, X. Tang, Aligned carbon nanotube–based flexible gel substrates for engineering biohybrid tissue actuators, *Adv. Funct. Mater.* 25 (28) (2015) 4486–4495.
- [107] L. Dykman, N. Khlebtsov, Gold nanoparticles in biomedical applications: recent advances and perspectives, *Chem. Soc. Rev.* 41 (6) (2012) 2256–2282.
- [108] G.F. Paciotti, L. Myer, D. Weinreich, D. Goia, N. Pavel, R.E. McLaughlin, L. Tamarkin, Colloidal gold: a novel nanoparticle vector for tumor directed drug delivery, *Drug Deliv.* 11 (3) (2004) 169–183.
- [109] N. Lewinski, V. Colvin, R. Drezek, Cytotoxicity of nanoparticles, *Small* 4 (1) (2008) 26–49.
- [110] J. Pérez-Juste, I. Pastoriza-Santos, L.M. Liz-Marzán, P. Mulvaney, Gold nanorods: synthesis, characterization and applications, *Coord. Chem. Rev.* 249 (17–18) (2005) 1870–1901.
- [111] N.R. Jana, L. Gearheart, C.J. Murphy, Wet chemical synthesis of high aspect ratio cylindrical gold nanorods, *J. Phys. Chem. B* 105 (19) (2001) 4065–4067.
- [112] S. Chen, Z.L. Wang, J. Ballato, S.H. Foulger, D.L. Carroll, Monopod, bipod, tripod, and tetrapod gold nanocrystals, *J. Am. Chem. Soc.* 125 (52) (2003) 16186–16187.
- [113] K. Kalishwaralal, V. Deepak, S.R.K. Pandian, S. Gurunathan, Biological synthesis of gold nanocubes from *Bacillus licheniformis*, *Bioresour. Technol.* 100 (21) (2009) 5356–5358.
- [114] J. Chen, B. Wiley, Z.Y. Li, D. Campbell, F. Saeki, H. Cang, L. Au, J. Lee, X. Li, Y. Xia, Gold nanocages: engineering their structure for biomedical applications, *Adv. Mater.* 17 (18) (2005) 2255–2261.
- [115] M. Shevach, S. Fleischer, A. Shapira, T. Dvir, Gold nanoparticle–decellularized matrix hybrids for cardiac tissue engineering, *Nano Lett.* 14 (10) (2014) 5792–5796.
- [116] S. Fleischer, M. Shevach, R. Feiner, T. Dvir, Coiled fiber scaffolds embedded with gold nanoparticles improve the performance of engineered cardiac tissues, *Nano-scale* 6 (16) (2014) 9410–9414.
- [117] M. Shevach, B.M. Maoz, R. Feiner, A. Shapira, T. Dvir, Nanoengineering gold particle composite fibers for cardiac tissue engineering, *J. Mater. Chem. B* 1 (39) (2013) 5210–5217.
- [118] R. Ravichandran, R. Sridhar, J.R. Venugopal, S. Sundarajan, S. Mukherjee, S. Ramakrishna, Gold nanoparticle loaded hybrid nanofibers for cardiogenic differentiation of stem cells for infarcted myocardium regeneration, *Macromol. Biosci.* 14 (4) (2014) 515–525.
- [119] S. Sridhar, J.R. Venugopal, R. Sridhar, S. Ramakrishna, Cardiogenic differentiation of mesenchymal stem cells with gold nanoparticle loaded functionalized nanofibers, *Colloids Surf. B Biointerfaces* 134 (2015) 346–354.
- [120] J.-O. You, M. Rafat, G.J. Ye, D.T. Auguste, Nanoengineering the heart: conductive scaffolds enhance connexin 43 expression, *Nano Lett.* 11 (9) (2011) 3643–3648.
- [121] S. Naseri, M. Diba, S. Golkar, A.R. Boccaccini, R.N.K. Taylor, Fabrication of gold–nanoshell/polycaprolactone composite films with high electrical conductivity, *Mater. Lett.* 130 (2014) 164–167.
- [122] T. Dvir, B.P. Timko, M.D. Brigham, S.R. Naik, S.S. Karajanagi, O. Levy, H. Jin, K.K. Parker, R. Langer, D.S. Kohane, Nanowired three-dimensional cardiac patches, *Nat. Nanotechnol.* 6 (11) (2011) 720.
- [123] P. Baei, S. Jalili-Firoozinezhad, S. Rajabi-Zeleti, M. Tafazzoli-Shadpour, H. Baharvand, N. Aghdami, Electrically conductive gold nanoparticle–chitosan thermosensitive hydrogels for cardiac tissue engineering, *Mater. Sci. Eng. C* 63 (2016) 131–141.
- [124] Y. Ganji, Q. Li, E.S. Quabius, M. Böttner, C. Selhuber-Unkel, M. Krasa, Cardiomyocyte behavior on biodegradable polyurethane/gold nanocomposite scaffolds under electrical stimulation, *Mater. Sci. Eng. C* 59 (2016) 10–18.
- [125] A. Navaei, H. Saini, W. Christenson, R.T. Sullivan, R. Ros, M. Nikkhah, Gold nanorod-incorporated gelatin-based conductive hydrogels for engineering cardiac tissue constructs, *Acta Biomater.* 41 (2016) 133–146.
- [126] Y. Li, X. Shi, L. Tian, H. Sun, Y. Wu, X. Li, J. Li, Y. Wei, X. Han, J. Zhang, AuNP–collagen matrix with localized stiffness for cardiac-tissue engineering: enhancing the assembly of intercalated discs by β 1-integrin-mediated signaling, *Adv. Mater.* 28 (46) (2016) 10230–10235.
- [127] K. Zhu, S.R. Shin, T. van Kempen, Y.C. Li, V. Ponraj, A. Nasajpour, S. Mandla, N. Hu, X. Liu, J. Leijten, Gold nanocomposite bioink for printing 3D cardiac constructs, *Adv. Funct. Mater.* 27 (12) (2017), 1605352.
- [128] R. Feiner, L. Engel, S. Fleischer, M. Malki, I. Gal, A. Shapira, Y. Shacham-Diamond, T. Dvir, Engineered hybrid cardiac patches with multifunctional electronics for online monitoring and regulation of tissue function, *Nat. Mater.* 15 (6) (2016) 679.
- [129] A. Mihic, Z. Cui, J. Wu, G. Vlacic, Y. Miyagi, S.-H. Li, S. Lu, H.-W. Sung, R.D. Weisel, R.-K. Li, A conductive polymer hydrogel supports cell electrical signaling and

- improves cardiac function after implantation into myocardial infarct, *Circulation* 132 (8) (2015) 772–784.
- [130] C.-W. Hsiao, M.-Y. Bai, Y. Chang, M.-F. Chung, T.-Y. Lee, C.-T. Wu, B. Maiti, Z.-X. Liao, R.-K. Li, H.-W. Sung, Electrical coupling of isolated cardiomyocyte clusters grown on aligned conductive nanofibrous meshes for their synchronized beating, *Biomaterials* 34 (4) (2013) 1063–1072.
- [131] P. Hitscherich, S. Wu, R. Gordan, L.H. Xie, T. Arinze, E.J. Lee, The effect of PVDF-TrFE scaffolds on stem cell derived cardiovascular cells, *Biotechnol. Bioeng.* 113 (7) (2016) 1577–1585.
- [132] X. Wang, X. Gu, C. Yuan, S. Chen, P. Zhang, T. Zhang, J. Yao, F. Chen, G. Chen, Evaluation of biocompatibility of polypyrrole in vitro and in vivo, *J. Biomed. Mater. Res. A* 68 (3) (2004) 411–422 <https://doi.org/10.1002/jbm.a.20065>.
- [133] M. Nishizawa, H. Nozaki, H. Kaji, T. Kitazume, N. Kobayashi, T. Ishibashi, T. Abe, Electrodeposition of anchored polypyrrole film on microelectrodes and stimulation of cultured cardiac myocytes, *Biomaterials* 28 (8) (2007) 1480–1485.
- [134] B.S. Spearman, A.J. Hodge, J.L. Porter, J.G. Hardy, Z.D. Davis, T. Xu, X. Zhang, C.E. Schmidt, M.C. Hamilton, E.A. Lipke, Conductive interpenetrating networks of polypyrrole and polycaprolactone encourage electrophysiological development of cardiac cells, *Acta Biomater.* 28 (2015) 109–120.
- [135] C. Puckert, A. Gelmi, M. Ljunggren, M. Rafat, E. Jager, Optimisation of conductive polymer biomaterials for cardiac progenitor cells, *RSC Adv.* 6 (67) (2016) 62270–62277.
- [136] Electroactive 3D materials for cardiac tissue engineering, in: A. Gelmi, J. Zhang, A. Cieslar-Pobuda, M.K. Ljunggren, M.J. Los, M. Rafat, E.W. Jager (Eds.), *Electroactive Polymer Actuators and Devices (EAPAD) 2015*, International Society for Optics and Photonics, 2015.
- [137] D. Kai, M.P. Prabhakaran, G. Jin, S. Ramakrishna, Polypyrrole-contained electrospun conductive nanofibrous membranes for cardiac tissue engineering, *J. Biomed. Mater. Res. A* 99 (3) (2011) 376–385.
- [138] L. Wang, J. Jiang, W. Hua, A. Darabi, X. Song, C. Song, W. Zhong, M.M. Xing, X. Qiu, Mussel-inspired conductive cryogel as cardiac tissue patch to repair myocardial infarction by migration of conductive nanoparticles, *Adv. Funct. Mater.* 26 (24) (2016) 4293–4305.
- [139] A. Gelmi, A. Cieslar-Pobuda, E. de Muinck, M. Los, M. Rafat, E.W. Jager, Direct mechanical stimulation of stem cells: a beating electromechanically active scaffold for cardiac tissue engineering, *Adv. Healthc. Mater.* 5 (12) (2016) 1471–1480.
- [140] H.S. Nalwa, *Handbook of Organic Conductive Molecules and Polymers*, Wiley, 1997.
- [141] D. Zhang, Y. Wang, Synthesis and applications of one-dimensional nano-structured polyaniline: an overview, *Mater. Sci. Eng. B* 134 (1) (2006) 9–19.
- [142] A. Borriello, V. Guarino, L. Schiavo, M.A. Alvarez-Perez, L. Ambrosio, Optimizing PANi doped electroactive substrates as patches for the regeneration of cardiac muscle, *J. Mater. Sci. Mater. Med.* 22 (4) (2011) 1053–1062 <https://doi.org/10.1007/s10856-011-4259-x>.
- [143] L. Huang, X. Zhuang, J. Hu, L. Lang, P. Zhang, Y. Wang, X. Chen, Y. Wei, X. Jing, Synthesis of biodegradable and electroactive multiblock polylactide and aniline pentamer copolymer for tissue engineering applications, *Biomacromolecules* 9 (3) (2008) 850–858 <https://doi.org/10.1021/bm7011828>.
- [144] S. Hosseinzadeh, M. Mahmoudifard, F. Mohamadyar-Toupkanlou, M. Model, A. Hajarizadeh, M. Adabi, M. Soleimani, The nanofibrous PAN-PANi scaffold as an efficient substrate for skeletal muscle differentiation using satellite cells, *Bioprocess Biosyst. Eng.* 39 (7) (2016) 1163–1172.
- [145] M. Mahmoudifard, M. Soleimani, S. Hatamie, S. Zamanlui, P. Ranjbarvan, M. Vossoughi, S. Hosseinzadeh, The different fate of satellite cells on conductive composite electrospun nanofibers with graphene and graphene oxide nanosheets, *Biomed. Mater.* 11 (2) (2016), 025006.
- [146] S. Hosseinzadeh, S.M. Rezayat, E. Vashegani-Farahani, M. Mahmoudifard, S. Zamanlui, M. Soleimani, Nanofibrous hydrogel with stable electrical conductivity for biological applications, *Polymer* 97 (2016) 205–216.
- [147] P.R. Bidez 3rd, S. Li, A.G. MacDiarmid, E.C. Venancio, Y. Wei, P.I. Lekes, Polyaniline, an electroactive polymer, supports adhesion and proliferation of cardiac myoblasts, *J. Biomater. Sci. Polym. Ed.* 17 (1–2) (2006) 199–212.
- [148] M. Li, Y. Guo, Y. Wei, A.G. MacDiarmid, P.I. Lekes, Electrospinning polyaniline-contained gelatin nanofibers for tissue engineering applications, *Biomaterials* 27 (13) (2006) 2705–2715.
- [149] E.G. Fernandes, V. Zucolotto, A.A. De Queiroz, Electrospinning of hyperbranched poly-L-lysine/polyaniline nanofibers for application in cardiac tissue engineering, *J. Macromol. Sci. A Pure Appl. Chem.* 47 (12) (2010) 1203–1207.
- [150] R.M. Moura, A.A. de Queiroz, Dendronized polyaniline nanotubes for cardiac tissue engineering, *Artif. Organs* 35 (5) (2011) 471–477.
- [151] H. Cui, J. Shao, Y. Wang, P. Zhang, X. Chen, Y. Wei, PLA-PEG-PLA and its electroactive tetraaniline copolymer as multi-interactive injectable hydrogels for tissue engineering, *Biomacromolecules* 14 (6) (2013) 1904–1912.
- [152] T.H. Qazi, R. Rai, D. Dippold, J.E. Roether, D.W. Schubert, E. Rosellini, N. Barbani, A.R. Boccacini, Development and characterization of novel electrically conductive PANI-PGS composites for cardiac tissue engineering applications, *Acta Biomater.* 10 (6) (2014) 2434–2445.
- [153] N. Baheiraei, H. Yeganeh, J. Ai, R. Gharibi, M. Azami, F. Faghihi, Synthesis, characterization and antioxidant activity of a novel electroactive and biodegradable polyurethane for cardiac tissue engineering application, *Mater. Sci. Eng. C* 44 (2014) 24–37.
- [154] N. Baheiraei, H. Yeganeh, J. Ai, R. Gharibi, S. Ebrahimi-Barough, M. Azami, S. Vahdat, H. Baharvand, Preparation of a porous conductive scaffold from aniline pentamer-modified polyurethane/PCL blend for cardiac tissue engineering, *J. Biomed. Mater. Res. A* 103 (10) (2015) 3179–3187.
- [155] R. Dong, X. Zhao, B. Guo, P.X. Ma, Self-healing conductive injectable hydrogels with antibacterial activity as cell delivery carrier for cardiac cell therapy, *ACS Appl. Mater. Interfaces* 8 (27) (2016) 17138–17150.
- [156] K.S. Ramadan, D. Sameoto, S. Evoy, A review of piezoelectric polymers as functional materials for electromechanical transducers, *Smart Mater. Struct.* 23 (3) (2014), 033001.
- [157] P. Aebischer, R.F. Valentini, P. Dario, C. Domenici, P.M. Galletti, Piezoelectric guidance channels enhance regeneration in the mouse sciatic nerve after axotomy, *Brain Res.* 436 (1) (1987) 165–168.
- [158] P. Martins, S. Ribeiro, C. Ribeiro, V. Sencadas, A. Gomes, F. Gama, S. Lanceros-Méndez, Effect of poling state and morphology of piezoelectric poly (vinylidene fluoride) membranes for skeletal muscle tissue engineering, *RSC Adv.* 3 (39) (2013) 17938–17944.
- [159] N. Weber, Y.S. Lee, S. Shanmugasundaram, M. Jaffe, T.L. Arinze, Characterization and in vitro cytocompatibility of piezoelectric electrospun scaffolds, *Acta Biomater.* 6 (9) (2010) 3550–3556 <https://doi.org/10.1016/j.actbio.2010.03.035>.
- [160] C.-W. Lam, J.T. James, R. McCluskey, R.L. Hunter, Pulmonary toxicity of single-wall carbon nanotubes in mice 7 and 90 days after intratracheal instillation, *Toxicol. Sci.* 77 (1) (2004) 126–134, <https://doi.org/10.1093/toxsci/kgf243>.
- [161] K. Donaldson, C.A. Poland, F.A. Murphy, M. MacFarlane, T. Chernova, A. Schinwald, Pulmonary toxicity of carbon nanotubes and asbestos – Similarities and differences, *Adv. Drug Deliv. Rev.* 65 (15) (2013) 2078–2086.
- [162] D. Cui, F. Tian, C.S. Ozkan, M. Wang, H. Gao, Effect of single wall carbon nanotubes on human HEK293 cells, *Toxicol. Lett.* 155 (1) (2005) 73–85.
- [163] K. Tamura, N. Takashi, T. Akasaka, I.D. Roska, M. Uo, Y. Totsuka, F. Watari, Effects of Micro/Nano Particle Size on Cell Function and Morphology, 2004 919–922.
- [164] A. Magrez, S. Kasas, V. Salicio, N. Pasquier, J.W. Seo, M. Celio, S. Catsicas, B. Schwaller, L. Forró, Cellular toxicity of carbon-based nanomaterials, *Nano Lett.* 6 (6) (2006) 1121–1125, <https://doi.org/10.1021/nl060162e>.
- [165] Y. Li, Y. Liu, Y. Fu, T. Wei, L. Le Guyader, G. Gao, R.S. Liu, Y.Z. Chang, C. Chen, The triggering of apoptosis in macrophages by pristine graphene through the MAPK and TGF-beta signaling pathways, *Biomaterials* 33 (2) (2012) 402–411 <https://doi.org/10.1016/j.biomaterials.2011.09.091>.
- [166] Y. Chang, S.T. Yang, J.H. Liu, E. Dong, Y. Wang, A. Cao, Y. Liu, H. Wang, In vitro toxicity evaluation of graphene oxide on A549 cells, *Toxicol. Lett.* 200 (3) (2011) 201–210 <https://doi.org/10.1016/j.toxlet.2010.11.016>.
- [167] W. Hu, C. Peng, M. Lv, X. Li, Y. Zhang, N. Chen, C. Fan, Q. Huang, Protein corona-mediated mitigation of cytotoxicity of graphene oxide, *ACS Nano* 5 (5) (2011) 3693–3700, <https://doi.org/10.1021/nn200021j>.
- [168] Y. Wang, Z. Li, D. Hu, C.-T. Lin, J. Li, Y. Lin, Aptamer/graphene oxide nanocomplex for in situ molecular probing in living cells, *J. Am. Chem. Soc.* 132 (27) (2010) 9274–9276, <https://doi.org/10.1021/ja103169v>.
- [169] J.H. Lee, Y.C. Shin, O.S. Jin, S.H. Kang, Y.-S. Hwang, J.-C. Park, S.W. Hong, D.-W. Han, Reduced graphene oxide-coated hydroxyapatite composites stimulate spontaneous osteogenic differentiation of human mesenchymal stem cells, *Nanoscale* 7 (27) (2015) 11642–11651, <https://doi.org/10.1039/C5NR01580D>.
- [170] L. Wang, Y. Wang, T. Xu, H. Liao, C. Yao, Y. Liu, Z. Li, Z. Chen, D. Pan, L. Sun, M. Wu, Gram-scale synthesis of single-crystalline graphene quantum dots with superior optical properties, *Nat. Commun.* 5 (2014), 5357. <https://doi.org/10.1038/ncomms6357>.
- [171] K. Yang, J. Wan, S. Zhang, Y. Zhang, S.T. Lee, Z. Liu, In vivo pharmacokinetics, long-term biodistribution, and toxicology of PEGylated graphene in mice, *ACS Nano* 5 (1) (2011) 516–522 <https://doi.org/10.1021/nn1024303>.
- [172] R. Shukla, V. Bansal, M. Chaudhary, A. Basu, R.R. Bhonde, M. Sastry, Biocompatibility of gold nanoparticles and their endocytotic fate inside the cellular compartment: a microscopic overview, *Langmuir* 21 (23) (2005) 10644–10654, <https://doi.org/10.1021/la0513712>.
- [173] C.M. Goodman, C.D. McCusker, T. Yilmaz, V.M. Rotello, Toxicity of gold nanoparticles functionalized with cationic and anionic side chains, *Bioconjug. Chem.* 15 (4) (2004) 897–900, <https://doi.org/10.1021/bc049951i>.
- [174] N. Ashammakhi, S. Ahadian, M.A. Darabi, M. El Tahchi, J. Lee, K. Suthiwanich, A. Sheikh, M.R. Dokmeci, R. Oklu, A. Khademhosseini, Minimally invasive and regenerative therapeutics, *Adv. Mater.* 31 (1) (2019), 1804041.
- [175] N. Ashammakhi, S. Ahadian, C. Xu, H. Montazerian, H. Ko, R. Nasiri, N. Barros, A. Khademhosseini, Bioinks and bioprinting technologies to make heterogeneous and biomimetic tissue constructs, *Mater. Today Bio* 1 (2019) 100008.